

Division Z 700  
.L 98

Section







## The Care and Repair of Books



# The Care and Repair of Books

BY

HARRY MILLER LYDENBERG


AND JOHN ARCHER



New York

THE R. R. BOWKER COMPANY

1931

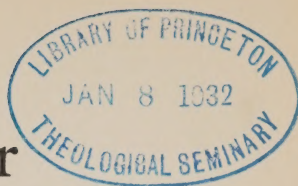


COPYRIGHT, 1931, BY R. R. BOWKER COMPANY

PRINTED IN THE UNITED STATES OF AMERICA  
BY J. J. LITTLE & IVES COMPANY, NEW YORK  
TYPOGRAPHY BY ROBERT S. JOSEPHY



## CONTENTS

i. The Care of Books in General	9
ii. The Care of Books in the Library	13
iii. Some Enemies of Books	21
iv. The Repair and Mending of Books	32
v. The Treatment of Paper, Vellum, etc.	65
vi. The Care of Leather Bindings	90
vii. The Treatment of Cloth Bindings	104
viii. Some Other Books	108
Index	123
Plate i	<i>facing</i> 42
Plate ii	<i>facing</i> 50

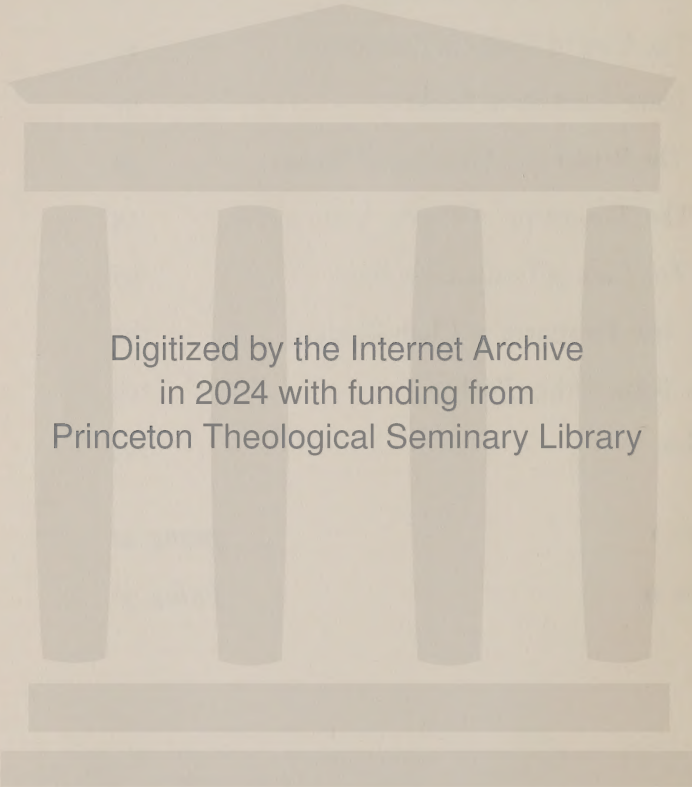

Digitized by the Internet Archive  
in 2024 with funding from  
Princeton Theological Seminary Library

## The Care and Repair of Books



## CHAPTER I

### The Care of Books in General

**B**OOKS are like children in more ways than one; in their response to care and attention in early life, for one thing, and in their response to heredity and environment, for another. It was the "Autocrat of the Breakfast-Table," was it not, whose first specification for his "man of family" demanded "four or five generations of gentlemen and gentlewomen"? For our "book of family" the same four or five generations of gentle forebears are equally necessary. The book's early life will be happier, its maturity longer, its final disappearance more distant if, like the child, it has found its lines cast among kindly and sympathetic friends and parents. Hygienic living conditions, proper prophylaxis, prevention of disease, are for both more important than medication or drugs. Thoughtful and skillful attention by competent, well trained, experienced physicians and surgeons is necessary for both.

The child has better assurance of long and useful life if he has been properly clad, has received proper



## The Care and Repair of Books

food and attention, has found his lot among people who will care for him and free him from unfair demands on his strength. The book has better assurance of long and useful life if it was brought into the world on paper of lasting quality, paper fitted to the needs the volume must serve, the demands it must meet. It will have better assurance of long and useful life if it is clad in protecting garments selected with judgment, cut and fitted with skill, certain of proper food at proper times in proper amounts, brought to appreciative hands as soon as indications of weakness begin to show themselves, treated with proper care and attention when major operations are called for, and housed under conditions most beneficial for such companions, helpmeets, friends.

For most of us the book is more like an adopted child than one of our own flesh and blood, since it usually reaches us full grown and mature. Our control over its youth and adolescence is usually slight. Happy the man permitted to stand by and help give shape and form to the child of his brain, to select type and paper, to choose boards and cover stock and end papers, to decide color and weight of cloth or leather, to sketch the lettering and decorations in this form or that.

## The Care of Books in General

With most of us the book must be housed under conditions over which we have less control than over many other more material things that enter into our daily lives. Our books are kept in houses as warm or as cool during the heating season as our wishes or financial means permit. But during the summer our houses are hot or cool, dry or damp, suffer harm or rejoice in favoring conditions that depend usually on the weather and are happily independent of our control. We all know they should not be too hot or too cold, too humid or too dry, but few of us are fortunate enough to be able to control these factors. Sunshine helps free our books from various enemies, but sunshine will soon deaden many modern papers and fade many modern colors in cloth or leather. Darkness protects from harmful effects of direct light, but darkness encourages molds and insect pests. With books or children or most other things the old Greek advice against "nothing too much" is as sound today as when first uttered. In the following pages an attempt is made to tell about some of the harmful influences that shorten the life of books, to suggest some remedies for cases that appeal for help, to plead for some of the care and attention for these mute but eloquent children of our brains that is given to the

## The Care and Repair of Books

children of our loins, to mitigate, if not remove entirely, the iniquities of the fathers visited upon books.

Various suggestions are here set down for the care and repair of books, manuscripts, broadsides, pamphlets, and other forms of the printed or written message. They have been developed from the actual handling of books and caring for books, are set down from experience rather than culled from other books. No doubt other good methods are mentioned in books or are known as tradition in the guild of book binders. The mere fact of omission here is certainly no reason why they should not be tried; occasionally one workman is able to succeed with materials and methods that spell failure for his brother at the bench beside him. The real test comes with repeated trials and consistent success.

It is only fair to point out that the methods of treatment here set forth are primarily applicable to conditions prevailing in the temperate zone of this western world, and probably would require adjustment to colder or hotter, drier or more humid countries. Principles of treatment would remain the same; the only changes required would be in details of methods employed to overcome adverse conditions.

## CHAPTER II

### The Care of Books in the Library

LET us suppose you have your books safely delivered new and fresh for current publications, in "good second-hand condition" for the older works, all well printed in a good face of type impressed on good paper, all protected by boards properly sewed in and properly covered with first class cloth or well tanned leather, all the work of competent artisans anxious to show the skill of their hands—a set of assumptions probably contrary to fact in most cases, but well enough to start with as a preliminary survey.

First comes opening the book. Well, opening books is nothing more than opening books, is it not? Nay, not so. Much harm has been hopelessly done to innocent volumes by careless or thoughtless or ignorant or indifferent handling when opening them. Your reader who really cares for books will put the volume on a table, the back down and the fore edges up, will open the front cover, then the back, will open a few pages next from the back and

*Opening  
the book*

## The Care and Repair of Books

the front alternately, pressing firmly but gently along the inner margins of the pages, thus lessening the danger of breaking the binding between the sections. If the book has been bound properly all this care may perhaps not be necessary. But the danger is that careless or improper binding may be so covered up that harm is done before it is discovered. Whether well bound or poorly bound there is not the slightest doubt as to the gratitude for careful and appreciative opening felt by the spirit treasured up within those covers.

*Collating* After the book is opened comes collating, not so portentous or imposing a task as the phrase may perhaps suggest. It means merely the making certain that the volume is complete and perfect, usually entailing nothing more than running through the pages one by one to see that all are there and to catch omissions and imperfections. If maps or plates are listed outside the pagination they must be checked for completeness and for proper placing. In early printed books careful checking of signatures and catchwords may be necessary. This is also the time to see if the cover is damaged, if the corners are bent or broken or battered, if the lining is loose. New books go back to dealer or publisher if not satis-



## The Care of Books in the Library

factory; with old ones decision as to return or repair will depend on circumstances.

Recording and accessioning and cataloguing offer the next hazard. In some private libraries these processes take place in the brain of the owner; in larger collections they become more complicated and more harmful. Some indication should certainly be made as to date of receipt, source, cost, and these notes can usually be added inoffensively and inconspicuously but securely. Some owners content themselves with a pencil note on a fly leaf or other blank page, on a margin of a leaf, on a bookplate, others religiously refusing to mark their books in any way and recording the necessary information on the catalogue card, shelf list, or some other similar document. It is a matter for the individual to settle, no council or supreme court having thus far been invested with authority to speak for all of us at all times in all places so far as books are concerned. A few libraries have bookplates and book traditions that add distinction to any volume once on their shelves. With most, however, it is safe to say that the less the marking the less the danger of harming. To be sure, if absence of marking increases the danger of theft the decision is simple. Some owners use a code in referring to source and

*Catalogue,  
accession,  
ownership  
records*

## The Care and Repair of Books

price, adopt a cryptic method of marking ownership by notation on certain inside pages, and thus lessen the danger of harm to the volume. The owner undoubtedly has the legal right to add his signature to title-page or fly-leaf; approval or objection will depend on the point of view of the person making comment.

*Stamps* Perforating stamps or rubber stamps are occasionally used, more often in public collections than private. Little defence can be offered except the obvious hope or belief that the book with them is spared a more distressing fate than the one without. At rare intervals there is occasionally found a stamp of size and appearance able to prove they are not necessarily all ugly or forbidding, but it means examination of many to find the infrequent attractive one.

*Life on the shelves* When once these preliminary records have been finished comes the next hazard in shape of the life of the book on the shelves. The shelves should normally be filled, or they should have enough book supports to keep the volumes standing upright. If they are too full it means rubbing and harmful friction, inevitable wear on the top of the back when books are pulled down; if not full enough the books will lean to one side or the other, and the bindings will be

## The Care of Books in the Library

harmful. This seems so slight a matter as frequently to be overlooked, but there are no more insidious or harmful enemies of books than the practice of letting them sag on the shelves. If there are any pamphlets or paper bound volumes among the lot their life is certainly neither long nor merry unless they are properly supported.

Book supports can be bought from any dealer in library supplies, or any man handy with tools can make them. You need nothing more than an upright held in position firmly enough to assure an upright position to the books next it. Commercial supports are frequently stamped out of a piece of metal cut in the centre and bent to form an upright section. Some have a flange and others not; the former are preferable, since the flange helps prevent the damage done when books are inadvertently pushed against the support as they are put on the shelf. Those with a hook protruding through the bottom of the shelf must be guarded against to make certain they do not harm tall books shelved below.

*Book  
supports*

A homemade support can easily be made by taking a piece of seven-eighths soft wood four or five inches long and four or five inches wide with a two by two by four block set at its base. Or a piece of sheet

## The Care and Repair of Books

metal may be set against such a base. In many ways the support used in the old Gore Hall days of the Harvard College library can not be bettered, and it was nothing but a common clay brick covered with stout paper. These homemade varieties suffer in competition with the commercial supports in bulkiness and waste of space, but to some booklovers their human touch has a distinct appeal as compared with the cheaper and more efficient machine product.

So far as that is concerned any collection will benefit if it has the advantage of attention by a pair of hands that get fun out of doing things, that like to explore the anatomy of books enough to give proper attention to small pieces of repair work, that know how to apply a strip of paste or glue to hold a signature in place or to set back a leaf that is breaking loose, that can fasten a label beginning to curl on one edge and will soon be entirely off unless securely restored once more.

*How books  
should not  
be shelved*

One of the quickest and surest ways to damage books is to shelve them on their fore edges. In any case there is the tendency, with large volumes the certainty, to loosen text from covers. Large books should be stored on shelves deep enough to hold them safely, on shelves fitted with proper supports. No exact fig-

## The Care of Books in the Library

ures can be set down as marking the precise size that ought to be kept flat on roller (or smooth metal) shelves rather than stand upright, but there certainly is no doubt that large volumes should be stored in a way to minimize friction in shelving or withdrawing them, should be kept either upright or flat, never half way, should be stored in a way to do no damage to themselves or to others.

When books are displayed in exhibition cases care should be taken to prevent their coming into direct sunlight. Pages exposed should be changed now and then. A sheet of plate glass over or in front of the book will do much to keep dust and dirt from the pages. If the case is dust proof fear may be set aside as to the effect of the confined air on the paper and other materials in the book. A constant condition of air, in itself, in the exhibition case will do little harm to the contents.

*Books in  
exhibition  
cases*

The private library suffers less danger to books while being handled than does the public collection with volumes bandied about between ignorant readers and thoughtless attendants. Housecleaning or moving does more harm to books in the private home than their normal use under ordinary circumstances. In the larger public collections they suffer

*Care in  
handling  
books*



## The Care and Repair of Books

sadly unless subject to constant, intelligent, sympathetic supervision. Few things are more dangerous than stacking books into shaky, unstable piles; a slight jar and they tumble to the floor. Tossing books like tennis balls or chunks of coal may conceivably amuse the youngsters thus diverting themselves, but it gives little benefit to the victims. If books have to be moved they should be packed stoutly enough to prevent friction or rubbing, loosely enough to prevent strain and stress, should be handled with thoughtful and intelligent care, be treated with the respect they deserve.

## CHAPTER III

### Some Enemies of Books

SOME enemies of books can be seen, and methods of control or remedy are obvious. Some of the most insidious, persistent, voracious, insistent attackers, however, can not be seen in operation, though their effects and results are plain even to the blind.

The air we breathe may be one of the worst enemies of the books we collect. It harms if too dry, it harms if too wet. When books are kept in rooms with air too dry their paper and leather turn brittle and begin to crumble. This should not happen, to be sure, and would not happen if paper and leather had proper resistance. Paper books and leather bindings have for ages existed in dry climates with no serious harm. But paper and leather of these later days are made to sell rather than to last; cheapness is more essential than permanence. Paper and leather and cloth for books play so small a part in the whole field of paper and leather and textile industry in the modern world that they are in no position to insist on obedience to their demands, even if these demands

*Harm  
from  
the air*

## The Care and Repair of Books

were sharply enough defined to be formulated. The book world therefore can do little more than take what is given to it in the general field, fortunately finding here and there a papermaker or a tanner who still has enough pride in craftsmanship to look on his calling as something more than a mere means to daily bread. Good paper and good cloth and good leather can be had by anyone willing to pay the price properly demanded by any workman called on to produce anything different from the ordinary. But such efforts are costly.

*Harm  
from  
dampness* This is all however very general as a comment on current conditions in the world of the making of books, and the specific question is what a book owner can do to keep his library from becoming too damp or too dry. Too much dampness means mold and mildew, loosening of paste and glue, weakening of fibres of paper and leather. This however is so unusual a situation outside the tropics or away from fogbound seacoasts that few readers will probably be called on to meet it. The remedy is removal of the humidity by artificial heat or by increased circulation of dry air. Frequent wiping of books with dry cloths, frequent treatment of leather bindings with some of the preparations mentioned in Chapter VI on Preser-

## Some Enemies of Books

vation of Leather Bindings, will serve as palliatives, but the best method of meeting the situation is artificial or natural control of humidity.

Most libraries in the United States and Canada will have more trouble in fostering and cultivating humidity than in driving it away. Most of us give more heat than is good for books, dry heat that drives the life out of paper and leather, dry heat that calls for mitigation of its dryness by means of artificial moistening of the air. This is largely a matter of attention and thoughtfulness and care in the ordinary household, or artificial conditioning of air in larger structures and institutions. If a house is heated by a hot air furnace it usually is simple to add hot water to the air as it leaves the firebox. With steam and hot water heating other methods must be used. Various devices are on the market for attachment to radiators to be filled with water and thus increase the humidity by evaporation. Some are simple, requiring little more than a daily thought to keep them filled; others are more complicated, occasionally more effective, certainly more exacting of time and attention. Some librarians have found satisfactory results from setting wet sponges in copper receptacles under their book cases. Others have turned to open vessels treated as

*Harm  
from  
dryness*

## The Care and Repair of Books

furniture or pieces of ornament. As a matter of fact the means is less important than the end, the securing of an average humidity of fifty to sixty or sixty-five degrees. A hygrometer or wet and dry bulb thermometer costs little and is simple to read. Occasional use of it, followed by efforts to take advantage of what it tells as to conditions, will benefit any collection of books. Bear in mind, however, that much water has to be evaporated to affect the humidity of a room heated to 70 degrees in cold weather. Keeping the temperature down is an excellent way to keep the relative humidity up.

### *Polluted air*

It is more difficult to ward off the attacks of noxious gases, more difficult to learn of their presence before their fell effects show themselves, more difficult to remove them or keep them out, quite as difficult to repair their ravages. Theoretically it is possible to care for such situations by conditioning the air, but this is a counsel of perfection possible only for buildings with ample mechanical equipment attended by intelligent and sympathetic and competent engineers. Even then it is largely a question of opinion as to the success of the equipment. For the small householder the only refuge seems change of residence. If he lives near a laundry or smelter or



## Some Enemies of Books

power house, or any one of a dozen other lethal instruments developed by our advanced civilization, he may be sure that day by day and hour by hour their chimneys and smoke stacks belch forth gases that pollute the air and are certain to take their toll of anything in his house composed wholly or partly of leather or paper. The city dweller is of course in a much worse situation in this respect than his brother in the country far removed from evidences of modern industrial progress. Community control of sewage disposal has progressed farther than community control of atmosphere pollution. No study of the economic waste and damage done to the book world in this way seems to have been made in a systematic fashion. An owner of good books who realizes he is living in a region subject to this air pollution will do well to think about his responsibility toward his books as well as toward his family.

Disease laden air is not infrequently charged with blame for damage to books. Just how much harm can be done to books by air borne disease germs is doubtful. An eye is frequently cast askance on books used by the sick or on books housed in rooms where sickness has laid its hand. It is perhaps not unnatural to assume that modern precautions would recommend

*Air borne  
disease  
germs*

## The Care and Repair of Books

disinfection, but it is safe to say that few cases of infection can be traced unquestionably to books. The best judgment calls for burning of books subjected to cases of anthrax and smallpox. It is the practice of the Department of Health of New York City to expose to fresh air and sunlight for forty-eight hours books in actual contact with patients during the infectious period of scarlet fever, septic sore throat, diphtheria, epidemic cerebro-spinal meningitis, poliomyelitis, encephalitis lethargica, and typhoid fever, followed by storage for three months. Books connected with patients suffering with these and other reportable diseases but not actually in contact with them are exposed to fresh air and sunlight for forty-eight hours.

*Tuber-*  
*culosis* Every now and then some earnest soul feels oppressed by the dangers to the community from books belonging to public libraries used by persons suffering with tuberculosis. The consensus of opinion now held by competent medical men seems to be that tuberculosis can not be spread in this way.

*Bedbugs*  
*and*  
*cockroaches* If bedbugs or cockroaches have taken a fancy to books exposure to the sun is usually sufficient to drive them away, for these pests thrive on dampness, darkness, warmth. Sunshine however will not solve the problem of destroying the pests in their homes or

## Some Enemies of Books

sterilizing eggs or larvæ. For this the safest step is to expose the books to some such agent as formaldehyde in an airtight chamber.

Bookworms and borers attack boards and paper, roaches eat the filler of the book cloth. Rats and mice eat the paste and glue.

Vermin like these are infrequent if not unknown in light, well ventilated rooms. They come sometimes in shipments from the tropics, and books from these regions should be quarantined before being shelved. Open the parcel in sunlight, for gentry of this sort have no love for the sun. If adults, eggs, or larvæ are found immediate action is called for. Kill the live ones, isolate the infected volumes, spray thoroughly with a solution of formaldehyde or corrosive sublimate. Any good insecticide, liquid or powder, may be used, but be sure it has been tested against discoloration of paper or book cloth. It may be necessary to call in a professional exterminator, but make sure beyond doubt that he has had successful experience elsewhere with books. Your library is no place for trial of his 'prentice hand. These professionals may usually be found in large cities. In smaller places it may be necessary to rely on local hospitals or the local health officer. It is needless to

*Other  
vermin*

## The Care and Repair of Books

remark that no gas such as formaldehyde, or any other effective as a disinfectant, should be used except under conditions assuring perfect control of agent and apparatus.

*Mildew or mold* Mildew or mold is a direct result of dampness and high humidity. It is a thin, whitish coating consisting of fungi of many kinds, and its action is unbelievably rapid. The best remedy is prevention, and the best method of prevention is storage in light, well ventilated rooms where the books are kept dry. All easy enough to say, to be sure, but what help has any owner of books against the humid heat that occasionally swoops down on hapless residents of the southern and eastern seaboard of this continent? Well, for one thing, he can shut the windows and turn on artificial heat, no matter what the thermometer says as to outside temperature. He must first drive away the humidity. Heat may be uncomfortable, but if it is dry the mold will not spread. Then rub the books with clean, dry cloths, and keep careful watch to see that no advance takes place. Most cases of mold or mildew can be removed from paper by alcohol if the stain is on the surface. Once into the fibres the case seems hopeless. The British Museum uses thymol for sterilizing.

## Some Enemies of Books

One of the most malevolent hostile acts books suffer from is well intentioned dusting or cleaning. Books ought to be kept clean, of course. No lover of books wants them to soil fingers or clothes or anything else connected with the reader. But no lover of books can ever think with any other emotion than horror and dread when he falls back or looks forward to their fate during the spring or fall housecleaning that splits so many happy families in this fair land. Dust on books may be unpleasant, but it certainly can do no such harm as the banging and thumping they get on these annual or semiannual incursions or on the weekly or monthly attacks of housekeepers and housemaids. A vacuum cleaner will remove dust, granted it is properly designed and is fitted with a proper brush for work of this kind and, in addition, is handled with a modicum of intelligence and thought. Dust cloths, with a slight sprinkling of oil, will remove the dust and prevent its being spread. Here, as in various other processes, the instrument is less important than the judgment that governs its use. Further study in this field of dust removal as applied to books may well be made. If it should prove to be a choice between permitting dust to accumulate and seeing the shelves and books

*Dusting  
and  
cleaning*

## The Care and Repair of Books

“cleaned” in ordinary slap-dash fashion there is no doubt as to the wisdom of choosing the former. How successful the owner proves to be in carrying through his choice is largely a matter of personality. Uncontrolled cleaning zeal can do much harm to books.

*Regular  
supervision*

Just as guardians of public and family health are more anxious nowadays to insure proper precautions and to develop preventive medicine than to indulge in heroic measures of restoration after disease has set in, so the owner of a library will fare much better if he has the books examined now and then by a competent workman to repair slight defects before they develop, and to help these mute companions of his quiet hours, these brave helpers in his efforts to spread knowledge of human life and thought, resist the harmful influences that snap at them from every corner of the room and from every pair of hands stretched toward them. It is an easy matter to see that leather bindings are kept in good condition; or, at least, it is much more easy to start afresh and see that they do not go backward, than it is to repair the damage when once it has begun its wicked work. Find a competent person, set him at a systematic examination of shelf after shelf, let him patch here and repair there as the patients call for help and



## Some Enemies of Books

attention, and at the end of the year the books will be in much better condition than if the need of binder's care is called to mind only when the case is so striking as to shriek its demands.

## CHAPTER IV

### The Repair and Mending of Books

**S**KILL in mending books depends to a certain extent on the knowledge the mender has of the way books are made. The more one knows about bookbinding materials, leather, paper, cloth, thread, paste, glue, the better the chances of success. How will the paper wear? Is it brittle or tough? How do paste and glue affect it? Knowledge of these and similar points, joined to practice in mending and repairing, will help mightily.

One is sometimes tempted to extend Punch's advice about marriage to the problem of mending books. Many books, to be sure, repaired by inexperienced hands, have been so sadly harmed that their old age is much worse than their youth. Far better to set them aside and wrap them up till they can be turned over to competent and understanding hands. But in many cases the life of books can be materially lengthened if intelligent first aid is given as soon as signs of ill health appear. After a book begins to break, its lesions call for practiced care and attention

## The Repair and Mending of Books

quite as obviously as torn skin or broken bones on the human frame. Book anatomy is not so complex or intricate as that of the upper vertebrates, to be sure, but the surgeon must have sympathy and training whether treating books or man.

There is no reason, however, why the average collector and lover of books should not make minor repairs—after he has learned how books are put together. His introduction to book anatomy should begin with dissection of useless cadavers rather than with attempts at vivisection. Take an old book obviously on its way to the waste basket, and see how much you can learn by study of its construction before you begin to use the knife. Note how the board or leather covers or backs have a layer of cloth or paper pasted over them for protection and ornament. See how the back is sometimes the same sheet as the cover, sometimes is another sheet of leather or cloth. Learn how the covers are fastened to the book; in older books you will find the signatures, or gatherings of leaves and pages, are usually sewn on bands or cords that are laced into the side covers, and in modern books you will see this connection is merely a thin sheet of “super” or muslin glued to the signatures on its one side and to the boards on the other.

*Anatomy  
of the book*

## The Care and Repair of Books

Come to know the difference between the sewing of signatures on cords and the overcasting of signatures to one another by stitches that may or may not hold securely. See whether the plates are pasted in or are folded in. Careful study and observation will help avoid many mistakes in attempting repairs.

When repair work really begins one of the first things needed is glue or paste. Books may be made without paper; many are made of leather or vellum and little else. Books may be made without cloth or parchment or binder's boards. But it is difficult—not to say impossible—to make them without glue or paste. And it is not easy to find any substance entering into the making of books we know so little about as we do about glue.

*Glue* is an organic substance obtained from skins, hides, bones, sinews of neat cattle, sheep, horses, and from other animals; some comes from the heads and bones of fish. Hide glue is usually supposed to give best adhesive qualities. Glue differs from paste in that it can be made to remain flexible when dry. Paste always dries brittle. It is the addition of glycerine and other elements that permits glue to dry flexible. Because it contains less moisture in its usable state and because it dries more quickly after application glue

## The Repair and Mending of Books

has advantages over paste in various kinds of work. For the backs of books flexible glue should always be used, because it will dry and remain strong, elastic, capable of bending without cracking. Under such conditions paste would be brittle when dry. So too the joints will soon crack, sometimes break, when they are opened or shut if a hard, brittle glue has been used. A high grade glue will have less odor, will be stronger, will cover more space than one of poorer quality.

Glue is usually bought in flakes, sheets, cakes, or pulverized form. It is heated in a gas or electric pot, and it should be softened by soaking in water before applying heat. As it burns easily a double boiler type of pot is usually best for heating; the danger of burning is thus avoided, and the hot water serves to retain the heat even after the original heater is turned off. The commercial bindery uses glue pots or glueing machines, which permit heat to be supplied constantly with accurate measurement or adjustment.

Paste is made from flour obtained from the grains of rye, wheat, corn, rice; from the husks, cobs, stalks of some of these plants; from various starches, dex-

*Paste*

## The Care and Repair of Books

ing a greater moisture content, in drying more slowly by evaporation as contrasted with the quick setting of glue as it cools. Paste is usually white, or nearly so, and it does not stain as glue is likely to do.

*When to  
use  
paste or  
glue* The experienced binder is never in doubt as to when to use glue or paste. The latter is chosen for paper and soft cloths, such as cambric, canton flannel, silk; for casing-in books, for end leaves, for mending and repairing torn pages. Glue is used for the backs of books, and for colored or sized book covering cloths. If paste should be applied to some book cloths it would soften the cloth and remove color, size, grain, this because of its moisture content. Binder's boards and leather permit either glue or paste, with due consideration to the kind of work and the results desired. On books bound in quarter or half leather flexible glue is used. Books bound in three quarters leather or full leather, with raised bands, call for paste, because it is slow in drying, and because it softens the leather with its moisture and permits the binder more time to handle the whole process. With books of this kind glue would prevent satisfactory handling of the leather, because it dries so quickly that the binder would not have time enough to stretch and pull and form the leather.



## The Repair and Mending of Books

Paste may be made out of flour and water, the success of the effort depending largely on the skill and experience of the hands that do the mixing. In general it will be simplest to buy the paste on sale by any reliable stationer or dealer in library or bindery supplies. The only difference between the paste you make and the paste you buy is that the commercial paste has a bit of preservative added to prevent its becoming rancid. If the cover is kept on tightly and water is added now and then, the paste will probably keep in good condition as long as any is left in the container. It will cost a few cents more than paste made from household flour, but the slight additional expense is far offset by greater uniformity and more general satisfaction.

*Making  
paste*

For a larger supply, or for the satisfaction some of us get out of actually seeing things grow and take shape, paste may be mixed in any convenient bowl. Begin on a small scale and take about half a cup of flour. Add cold water gradually, stirring constantly until water and flour are blended, all lumps smoothed out, the mixture just about the proper consistency for gravy, for instance, not so fluid as soup nor so viscous as bread dough. Then add boiling water, put on the fire and bring the mass to a boil for

## The Care and Repair of Books

about one minute, stirring constantly. If it becomes too thick add sufficient warm water to bring it to proper consistency. Count on its thickening ten to fifteen per cent. as it cools. It should not run so freely as milk, should not be lumpy, should not be so stiff as to fail to run from the brush with moderate ease. Starch may be used instead of flour, entirely a matter of preference, price, convenience.

Dry paste can be bought in pound packages and larger quantities, requiring little more attention than adding water, and stirring. This is what most paper-hangers use. The commercial binder frequently mixes his paste in a machine, using special flour that permits adding hot water at once; but he uses paste in quantities far beyond the needs of the reader who turns to this book for help.

However, even if commercial paste is more satisfactory, do not adopt it exclusively until you have made enough paste to satisfy yourself that you actually can make it. Even if you buy your paste you will be in better command of the situation if you know how to make it. You certainly should learn by experience how much moisture is best for your work; the drier the paste the less danger of wrinkling, but if too dry it will not bind.

## The Repair and Mending of Books

In using paste remember that the less you use the better. The normal tendency is to use too much. A thin coat of any adhesive firmly pressed into the pores of the objects to be joined will hold the sheets more successfully than a thicker lot that has little more than its own portions to stick to and rapidly grows weaker and more brittle the drier it gets.

Remember too that paste contains moisture, which means that the pasted sheet has a tendency to curl or wrinkle. Pressure is needed to force the paste into the paper fibre for one thing, and for another to keep the paper smooth while it dries. If too much is applied some of it will squeeze out beyond the edges, which may cause other pages to stick together or may soil portions difficult to clean. Experience and experiment will show when there is too little or too much, when it is too thin or too stiff. The more practice on books and paper that mean little the more certain is good work on books and paper that mean much.

Paste may be applied with thumb or finger, if nothing better is near, but in the long run a good brush pays for itself. Paste brushes are made of the hair of horse tails, pigs, wild boars, the latter the best. They are softer than glue brushes, flat rather than

## The Care and Repair of Books

round like glue brushes, need little care and attention other than regular cleaning after use, and ought to last for a long time. Hang them up when not in use, or keep them flat, to avoid forcing the hairs to take a "set" and get permanently out of shape.

### *Repair equipment*

And that brings up the question of materials and equipment in general. First comes a table. Any kitchen table will probably be satisfactory; all one needs is a level, smooth working space fixed at convenient height, 30 to 36 inches from the floor, depending on whether you prefer to work sitting or standing. The materials noted below may be secured from any supply house dealing in bookbinding materials. Some dealers in library supplies sell repair kits and mending outfits put up in handy and attractive containers.

Here is a list of some of the things helpful in repair of books:

bone folders, 2 or 3

knives, one with the usual cutting edge, one with  
bevel edge for paring

scissors, one with 5-inch blades, one with 7-inch  
blades

sheet zinc, for cutting cloth, leather and paper

## The Repair and Mending of Books

straight edge, about 18 inches long  
plate glass sheet, about 18 inches square  
paste brushes and paste pot  
sponges, several  
book paper, several kinds  
blotting and wax paper, several sheets  
bond paper, for guarding plates  
tissue paper, for mending  
cambric and book cloth, several yards  
press, about 12 by 15 inches in size  
weights, which can easily be made by covering  
bricks with stout wrapping paper

Torn pages probably mark the first injury to a book, and they may be mended in any of the following ways:

*Torn pages*

If the tear does not affect the printing, cut a strip of thin, tough paper half an inch wide, a little longer than the tear. Cover the strip with paste and then lay it carefully on the paper over the tear, being sure to see that both edges of the tear have been brought together evenly. The strip should project slightly beyond the tear on the sound side of the paper and slightly beyond the edge also; trim the overhang along the edge with a pair of shears or scissors. A

## The Care and Repair of Books




good way to paste mending strips is to spread the paste evenly on a piece of glass (preferably plate) and lay the strip on it. Lift the strip and enough paste should adhere to it, just enough, not too much, not too little.

When the tear extends into the print put a small bit of paste on the torn edges and place them together. Then take a piece of soft mending tissue paper and rub it gently over the tear in a way to make the tissue adhere to the torn edges. Then put it into press or under a weight until it is dry. Tear off the superfluous tissue, taking care always to pull toward the tear from both sides. The delicate soft fibres of the tissue act as a binder, and when the task has been well done it is almost impossible to see how the binding has been accomplished. Here again it is practice that counts, and the first efforts should be made with books and torn pages that can afford to be spoiled.


---

*Plate One:* SOME TOOLS USED IN BOOK REPAIR AND RESTORATION  
1. Color dish. 2. Magnifying glass. 3. Small dish for color or paste. 4. Sandpaper block. 5. Earthenware cup. 6. Sponge. 7. Enameled tray. 8-13. Steel scrapers, creasers, probes, etc. 14. Bodkin. 15-20. Brushes. 21, 22. Tweezers. 23, 24. Dividers. 25. Knitting needle. 26, 27. Awls.



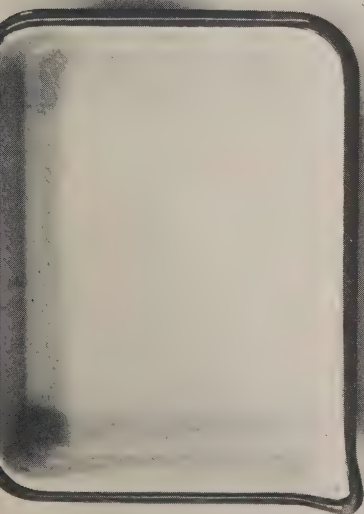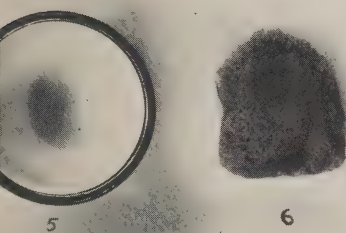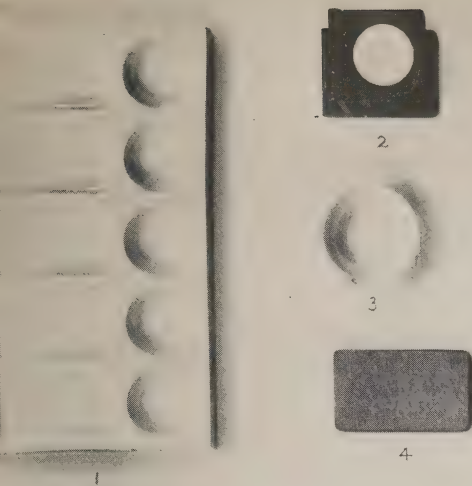

7

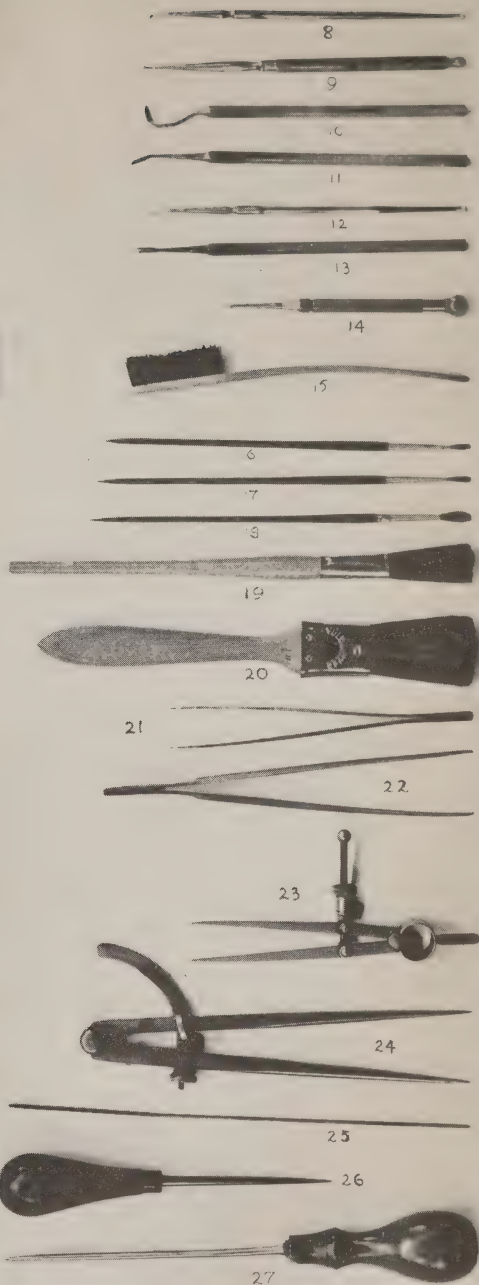



## The Repair and Mending of Books

The private library will but rarely have newspapers to be treated, and under ordinary circumstances such volumes should go to the professional binder. He will be best able to tell whether the cost of the repair is worth the effort. For the amateur gummed tissue stands out as first aid material, but this is particularly a case where restraint is necessary. The normal tendency is to use it on everything, books, newspapers, periodicals alike, and the danger is that it will show a yellowish color, darkening with age. It is safer, though less easy, to use tissue paper and white flour paste.

*Repair of  
news-  
papers*

Printed or manuscript sheets will often be given longer life if they are covered with some protecting fabric. This means lessening of legibility, to be sure, but the protection of the surface is usually well worth that price. And the legibility need not be reduced to an improper extent if judgment and care are used.

Though this treatment may, in cases of emergency, be given sheets in a bound volume the ideal is to take the book apart and handle the sheets flat. Silk or Japanese tissue paper may be used. Silk costs more and does less harm to legibility. Tissue costs less, is not so transparent as silk, gives more protection from

*Covering  
with silk  
or tissue  
paper*

## The Care and Repair of Books

the air. When either is used both sides of the page must be covered; otherwise it is certain to curl, due to the unbalanced pull of the covered side when but one side is treated.

*Paste* For an adhesive make a paste from pure wheat or rice flour, neutralizing it in color by a small quantity of tapioca dextrine. The thinner the paste the better. But if it is too thin it will not bind, and if it is too thick it shows lumps and gives an uneven result. Experience and good judgment are the only guides. Some paper calls for thin paste and some for thicker.

*Silk or chiffon* Spread a thin layer of paste on a sheet of glass. Lay a sheet of chiffon (about an inch larger in all directions than the sheet to be treated) on the pasted glass. Give this sheet another coat of paste and lay the paper on it, using the paste brush to smooth it down and insure complete contact. Give another coat of paste, and then lay on the second sheet of chiffon, carefully smoothing it down with the brush. Next strip all three sheets from the glass, an easy and simple task for the experienced hand, but not so lightly undertaken by the beginner. However, if previous warnings have been followed, the first trial at this sort of work will be with material of no great importance, and it will call for no great amount of

## The Repair and Mending of Books

effort before one begins to get confidence and to handle the wet, sticky sheets with ease and assurance. Hang the sheet on a rack, frame, or line already provided. When it is half dry place it between wax boards, put it to press for half an hour, strip the sheets from the wax boards, put them between new wax boards till fully dry, and then press them once more, overnight or for several hours. When dry the overhanging edges of silk should be trimmed even with the paper.

If there is much mounting or patching to be done it may perhaps be best to finish that part before beginning to paste the entire sheet. Slight repairs may be made while the sheet is on the pasted glass before the final sheet of silk is laid down. There is danger here, however, that the paste may dry and spoil the job. Here again experience must be the teacher.

The process is about the same when using Japanese tissue, except that pasted sheets are hung up to dry instead of being placed between wax boards and blotters. They are pressed when fully dry, and run through a heated mangle to press them still further and to make them as smooth as possible.

In the larger cities silk and paper for this purpose can be secured from wholesale dealers in textiles or

*Japanese  
tissue  
paper*

*Dealers*

## The Care and Repair of Books

paper, either direct or through a dealer in bindery supplies. In smaller places the binder will probably have to turn to his jobber or general supply house. Albert E. Oberfelder, 307 Fifth Avenue, and the Japan Paper Company, 109 East 31st Street, are New York city dealers in chiffon and tissue paper.

### *Other transparent materials*

It is not impossible that help in solving this problem of covering paper may be found in the use of cellophane or some of the other similar transparent materials made from cellulose. At present, however, all it seems safe to say is that if they do help they also call for development of a new technique in handling. They have not proved satisfactory when used in ordinary fashion by trained and competent workmen experienced in traditional binding processes. Time and experiment may develop the solution. From Boston comes the cheering report that special machinery is now in operation there giving every indication of success, but it is not easy to find satisfactory specimens of material treated in this way now standing the test of everyday use. Good wishes and earnest hopes of success must certainly be extended by all users of books and book papers to the optimistic inventor and aggressive developer.

But, to go back to mere methods of binding, re-



## The Repair and Mending of Books

member—it can not be repeated too often or emphasized too much—that whenever paste is applied for mending, the sheet or the volume must be put in press or kept under a substantial weight until it is completely dry. Wrinkling is otherwise inevitable. To keep the leaves from sticking together use waxed paper.

Loose leaves may be inserted in several ways. One is to lay the leaf flat on the table alongside the book. Cover it with a sheet of waste stock, except about one-eighth of an inch along the inside margin. Hold the covering sheet carefully and run the paste brush along the margin; the covering sheet will prevent the paste spreading over the page. Lift the waste sheet and place the sheet for insertion inside the book so that the pasted edge will adhere to the adjoining leaf in the book. Protect the pasted portions by waxed paper, and press till dry.

*Loose  
leaves*

If the page to be inserted threatens to project beyond the fore edge when finished the obvious remedy is to cut off the projecting part. A better plan is to fold the inner margin slightly, say about one-eighth of an inch, paste the turned over part, insert and press. This has the advantage of using the fold as a hinge, which is, however, dangerous and inad-

## The Care and Repair of Books

visible if the paper stock is brittle, weak, or poor. In such a case it will be best to cut the leaf and bind it to the stub by means of a paper hinge or thin cloth.

### *Repairing corners*

With a page that has lost a corner try to get a sheet of paper of the same stock, weight, color as the remaining portion. Lay it under the sheet and with a pencil lightly trace on it the outline of the missing part. Then tear it in a way to give a corner with two straight edges and an inside edge roughly following the pencil line, this corner to have its inside edge about one-eighth of an inch farther from the outside than the pencil line; the torn part should show an irregular bevel or feather edge. Paste the bevel edge, lay it on the corner, protect the sheets with wax paper, put the book to press, and trim with scissors when dry.

### *Filling holes*

If a page has had a hole torn in it, losing a picture or part of the text, for instance, the ideal is to replace it by a perfect copy of the same page from a book otherwise imperfect. If no such page can be found the hole may be filled by a "window" of onion skin or bond paper. Take a sheet of this kind of paper, lightly mark on it the outline of the tear, bevel the edges of the original page and the replacement sheet, paste, join, protect, and press. The "window" or inlay

## The Repair and Mending of Books

thus made will prevent further tearing as the page is turned.

Sometimes new books, fresh from the publisher, show loose covers. Perhaps the paste dried in the machine, and the book went through before the fact was noticed. Perhaps it fell on its edges, or perhaps it was opened roughly or was bent too much in the middle. Open the volume carefully, and spring the hollow back of the cover away from the "bone" of the book. If there is space enough use a long, thin brush to apply paste. If the opening is too narrow for this get a knitting or crochet needle to carry the paste to the parts that need it. Close the volume, rub the back with a bone folder, and put it away to dry.

*Loose  
covers*

It is at the hinge or joint where a book gets most wear and strain. Every time it is opened friction and tension are set up in the hinge. The basis of the hinge or joint is the material connecting the body of the book with the covers. Formerly the book was sewed to cords that were laced into the covers, and it was these cords that were flexed every time the backs or covers were opened or closed. Not so long ago came the discovery that manufacturing costs would be lessened and manufacturing time would be speeded if book and covers were connected by means of thin

*Hinges  
and joints*

## The Care and Repair of Books


cloth, called "super," glued first to the "bone" of the book and then to the insides of the cover boards. This strip of "super" is ordinarily about as long as the book is high, and is wide enough to project about half an inch or a full inch beyond each side of the back. It has but little strength, is thinner and more frail and fragile than cheesecloth, and pleads eloquently for care and attention when the book is handled. If to this weakness and thinness weak or brittle glue is added it is plain to the blind that expectation of life is short.

*Recasing* When this "super" gives way and the book breaks away from its cover the usual thing to do is recasing unless complete rebinding is necessary. The first step is removal of all cloth, paste, glue from the back. Sewing should be examined to see that it is intact. End papers should be stitched on the back and front. Take a piece of medium weight canton flannel or muslin as long as the book is high and two inches

---

### *Plate Two:* SOME TOOLS USED IN BOOK REPAIR AND RESTORATION

1-6. Knives for cutting cloth and leather. 7-9. Scissors.  
10. Lance point knife. 11. Sharp nosed cutting pliers.  
12. Thin bladed paper knife. 13-15. Mount cutting knives.  
16, 17. Folders and creasers. 18. Small bookbinder's hammer.  
19-21. Folders and creasers.



1



2



3




4




5



6

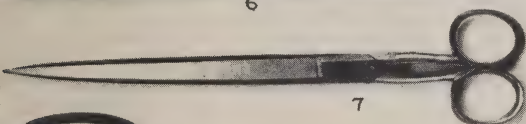

7

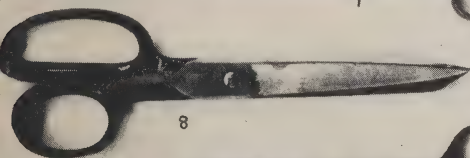


8




9



10

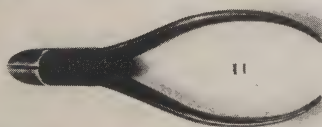

11



12



13




14




15



16



17

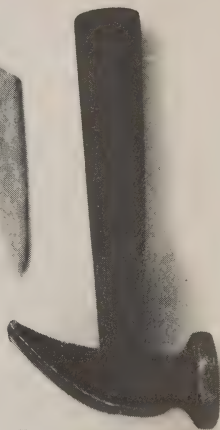

18



19



20



21





## The Repair and Mending of Books

wider than the back. Paste this to the back, which has just been given a coat of flexible glue. The cloth, if properly put on, will extend one inch on both sides of the back. It must then be rubbed down smooth and firm with a bone folder, and be put aside till dry. End papers and projecting pieces of cloth must be trimmed flush with the book. Lay the book in its case, open front cover, paste end paper, close and open the back cover, pasting the other end paper, close the book, put it between boards and into press till dry. To prevent end papers sticking to each other put wax boards between them and the text, both front and back, before putting the book to press. This "recasing" is a pretty piece of work when done by competent hands. Sober old age advises, however, that cheap and unimportant volumes be used for experimenting.

That is all well enough for a present-day "trade" book, but if the volume has a modern loose or spring back different methods must be followed. A tube or loose back must be made by folding back on itself several times a strip of strong hardware or kraft paper, just as long as the book and wide enough for three folds. First cover the back with glue, and lay this strip of paper on it, edge of the paper along one

*Loose  
backs*

## The Care and Repair of Books

edge of the back. Rub it down smooth. Fold the paper back on itself and run a narrow (say, about a quarter inch) line of glue along the exposed edge of the sheet as glued to the book. Use this glue to fasten the part of the paper just folded back to the edge of the sheet first glued to the back. Then fold the sheet back once more, this time along the original edge, glueing this folding to the sheet formed by the second folding. You thus have one part of the sheet glued to the back, another part folded back on this first part, a third part glued to the second part, the first part and the second part being free except at the fold and the edge where the two are glued together. Cut off any part of the sheet that projects. Open the free part with a bone folder, and you have the foundation for your hollow back. It is not quite so complicated as it sounds, and if you can watch a binder do it once you will have no difficulty in following him.

And now for the back. Glue a strip of cambric or muslin two inches wider than the back to the outside of the thrice folded strip of paper. Then paste the new leather back to the cloth, and you will have a loose back on the book instead of a tight back.

Tight backs are usually found on old books; loose

## The Repair and Mending of Books

backs generally mark more recent binding. A tight back is stronger than a loose back, but it can not be used with cloth bound books, because the flexing as the book is opened cracks and creases cloth, whereas leather in good condition is supple and flexes easily. A thin volume on thin paper will do better with a tight back, a thick volume on thick paper will stand up better with a loose back.

*Tight  
backs*

Sometimes the call comes for rebacking and re-binding, usually in the case of books of special interest for any one of a dozen reasons. Little more is called for than experience and skill on the part of the binder, two things easy to call for but less easy to secure. If he knows his business he will remove the original cloth, the end papers too if necessary, though this adds to the difficulty. The signatures may then be re-sewed or individual sheets repaired, as the case may call for. New backing is then applied, new boards or covers provided, and the old cloth and end papers pasted to the boards. Sentiment—or other considerations—sometimes calls for use of as much of the original cover as possible even if parts are worn or broken. In such a case the volume is rebacked or re-bound, as much of the old cover replaced as is consistent with good work, and the vacant spots merely

*Rebacking*

## The Care and Repair of Books

proclaim that a piece of restoration has been done. A good piece of craftsmanship deserves praise so long as no attempt at deception has been made. Repairing books is commendable, honest restoration is praiseworthy, work of this kind done to fool the unwary speaks for itself.

You may, however, have a book bound in leather, and for one reason or other wish to save the old leather on the back and the sides, replacing the worn leather in the hinge with the new. Or, you may find the old leather so far gone as to make it impossible to use it, but you want it replaced with new on back and hinge.

*Saving  
original  
leather  
backs*

In such a case the old leather must be taken off as carefully as possible. If the book has a loose back the problem is simpler than if the leather is glued tight to the back. It likewise is simpler if the volume is comparatively modern than if it is one of the old fashioned type with signatures sewed to cords or raised bands. Lift off the old leather with a thin, flat knife, and set it aside for future use if fortune favors and permits removal entire with no breaks or tears. Sometimes the leather is so old and brittle that breaking is inevitable, but sentiment or other consideration calls for its return to the volume. It is then removed

## The Repair and Mending of Books

in pieces as large as possible, these pieces being set aside for reassembling later and pasting on the back.

The leather is now all off the back or bone of the book. Next comes the work on the leather on the boards or sides. This is then lifted up with a thin, flat knife if there is any danger of breaking the skin by use of the ordinary bone folder. At this time it may be well to lift up the parts of the end leaves that cover the turn-over part of the leather. Moistening the end sheets will soften them and permit their being turned or lifted up without harm.

And now for the replacement. A piece of new leather should be chosen, as near the old in color and texture as possible, two inches wider and one inch taller than the old back. Pare its edges, a little more at top and bottom than along the side. Then give it a coat of paste, and fasten it to the back of the book. It is needless to remind you that the back should ere this have been thoroughly cleaned of all old paste, glue, and leather. Brush paste into the slits of the boards from which the old leather was taken, and then insert the sides of the new leather, working them under the old leather left on the boards but lifted carefully by the knife or bone folder, as just mentioned a moment or so ago. Now turn in the top

## The Care and Repair of Books

and bottom of the new leather, working them under the end leaves.

Rub all joints smooth with a folder, place wax boards or sheets of paper between the end leaves and the boards, put the book to press until it is thoroughly dry. If the paper along the inside joint has been torn or worn it may be necessary to paste a strip of similar stock along the joint, keeping the book open while these strips are drying.

Then carefully paste the old back to the new if it was removed without tearing, or match the pieces of the old leather back and paste them on in a way to make them match and give the original appearance. Rub them down and put the book to press for final drying. After it is taken out comes the time for inspection of new leather at the joints. If the shade matches nicely, well and good. If not, then comes a session with brush and pot of stain to make new and old live together in peace and quiet.

*Inter-leaving* Interleaving prevents much wear and tear to the material thus protected. As a first step towards this interleaving paste a strip of strong thin paper, preferably Japanese vellum along one side, using a strip about an inch and a half wide and two inches longer or higher than the piece to be protected. This makes



## The Repair and Mending of Books

a stub or hinge. Treat in this way all the pieces to be handled, and then lay them between sheets of durable all-rag paper at least one inch larger, top and bottom and on both right and left sides, than the largest of the pieces to be protected. If the interleaving is done with single sheets they must be oversewed, but if it is done with sheets folded into sections, they may be sewed through the fold and bound like any other book. This protection will undoubtedly lengthen the life of any mounted specimens, and will permit the book to be opened without danger of harm when it is laid flat for photographing or for exhibition.

Labels sometimes have their lettering marred or scratched off. They may be replaced by new ones after the remains of the old one have been carefully removed by means of a knife or scraper. New labels should be cut from paper or leather. Paper offers less difficulty than leather, as the leather must be washed with a size of thin paste to make it take the marking ink properly. Lettering should be put on the label and be perfectly dry before the label is pasted on the book. When it is safely dry and fast on the book it may be gone over with a protecting coat of thin book varnish, lacquer, or shellac.

*Labels,  
paper and  
leather*

## The Care and Repair of Books

*Restoration  
of  
book cloth*

Stained or faded book cloth may be restored by application of a water color stain or size of proper tint. Make it by dissolving a tablespoonful of white of egg in a cup of water. Allow twelve hours for complete absorption. To this add a tablespoonful of paste, and enough color soluble in water to give the necessary shade. Strain it through a very fine sieve or thin gauze, and then apply with a small brush or soft sponge.

*Water-  
soaked  
books*

With books water is an excellent servant but a most harmful and dangerous master. It is used at many stages of the manufacture of paper, and the stock retains its affinity for water through almost its entire life. When paper is made into books water, however, is one of its greatest enemies. Warped covers, swollen and stained, pages wrinkled and creased mark the afterlife of the book exposed to water. Heavily sized paper, coated with starch or glue or clay, is ruined by contact with water. The size, softened by the water, causes the pages to stick to one another, and if they dry in this state the book is a solid mass. Try to separate the pages, and the surface coating pulls off from the centre, destroying the print, and the only fate for the volume is fireplace or waste pile. Books made of better paper will stand

## The Repair and Mending of Books

wetting with less serious damage, but their pages inevitably wrinkle and swell distressingly. This may be helped by dampening a few pages at a time with a moist sponge, smoothing down the wrinkles and creases, putting the pages between dry blotters, and allowing them to dry under pressure. Repeat with a few more pages till the whole volume has been treated.

If a book has been thoroughly soaked it will probably be best to take it apart, smooth out the single leaves, drying them under pressure, collate and bind once more. When this must be done the paper will probably need resizing, as described on page 70. Paper in contact with water will nearly always be stained. Most of this staining will be removed in the sizing bath, but when sheets are not sized the stain may frequently be removed by judicious use of soap and water applied with a soft sponge. When doing work of this kind undamaged pages must be protected by wax boards and blotters.

Books damaged by fire offer various problems. If the covers are charred and the boards intact, scrape off the char from the covers and paste a new outer cover over the boards. In some cases it may be best to take the old cloth off entirely and recase the vol-

*Damage  
by fire*

## The Care and Repair of Books

ume. If edges are merely charred scrape them clean with a steel scraper and then use sandpaper to get a smooth surface. Gilding or marbling will probably remove all traces of the accident. When scraping the edges put the book in a press or vise. If the margins permit trimming take the book out of the cover, trim top and bottom and fore edges with hand or power cutter, and then recase it.

If the text has been damaged and it is worth the expense the charred edges may be trimmed off to uniform size and each leaf be inlaid, the whole then being sewed and rebound. Or it may seem best to remove the char, fill in damaged spots with fresh paper, mount each page between silk or tissue paper sheets, and then rebind. If damage has been limited to but a few pages, take them from the book, repair, insert on stubs left for the purpose.

When fire has made the paper so brittle that handling becomes difficult the sheet may be sprayed with a solution of gelatine size. The size should be hot, driven through a hand or power sprayer, and may be made according to the instructions set forth on page 70. This will give a coating to the surface of the paper, holding the brittle fibres together. Sheets so treated should be covered with silk or tissue paper.

## The Repair and Mending of Books

The best ink remover is frequently a sharp steel eraser wielded by a skilful and competent hand. If the ink has penetrated too deeply into the paper for removal by this means try the commercial ink eradicators obtainable at any stationery dealer's. They are usually two liquids, one an acid and the other chloride of lime. The latter added to the acid gives off free chlorine which bleaches the chemicals of the ink.

*Ink  
removal*

India ink yields to none of the chemical removers. If the steel eraser can not scrape it away better give a sigh and cover the spot by a sheet of paper pasted over it.

White lettering ink is soluble in water. It is used for lettering dark colored surfaces. Libraries sometimes use it for indicating class marks, call numbers, authors, various other things on the backs of books, sometimes protecting the entry by a coat of varnish or shellac. Alcohol will remove the varnish, and water can then be applied to the ink. This is all well enough for removal of the ink, but with the ordinary book cloths alcohol and water soften the filler of the cloth and start the colors to running. If there is danger of this better try the steel eraser.

*White ink  
removal*

Mutilation or disfigurement by pitch or tar is fortunately not frequent in books. It does happen now

## The Care and Repair of Books

*Pitch, tar,  
and wax  
stains*

and then, and the steel eraser is the first resort. After as much has been removed by this means as possible, try turpentine for the next step. Be careful to see that the tar does not dissolve out of hand when the turpentine is applied, and spread to do more damage. After the tar has been thoroughly softened by the turpentine and the page seems clear wash the sheet carefully with benzene. Wax should likewise be first scraped with the steel eraser. Then wash it with benzene, applied with a swab of cotton wool. This does not apply to sealing wax, which is proof against every chemical that will not harm the paper. The steel eraser or scraper is the only hope in such a case.

*Solander  
or slip  
covers*

Every now and then a book calls for treatment on account of its binding or cover. Sometimes a pamphlet must be cared for without binding, or the owner may wish to keep the unsullied sheets just as they came from the press or folder. For the first type a case or cover of some kind must be made; for the second there is a bit more variety of choice. A solander case gives best protection for bindings. This takes its name from the eighteenth-century Swedish botanist who became keeper of the Natural History Department in the British Museum and developed this form of protection. The solander case furnishes complete



## The Repair and Mending of Books

covering for the volume, stands upright on the shelves, is divided into two parts, the lower one with a neck over which the upper one fits. The cover should fit the book rather snugly, and the leather should be about the same in quality and color and finish as that of the volume to be protected. This is one of the most expensive cases to make, and likewise is one of the most satisfactory so far as protection is concerned.

There are many other forms of slip covers, cases, boxes, jackets, wrappers, all to be made out of paper, cloth, or leather, and all of cost and amount of protection afforded rising as the choice rises from the first to the third. Satisfactory making of a cover of this kind is a pretty test of the skill and judgment of a binder. The amateur can give himself much amusement and instruction by trying to make covers out of binder's boards, using paper or cloth for decorative finish.

Sometimes the binder is confronted with a book printed on paper of such poor quality as to defy sewing or any other form of binding, yet of such importance as to call for preservation. In such cases life may be lengthened, if not assured of immortality, by making a box, with hinged or slip cover or sides,

## The Care and Repair of Books

of fitting size to hold the volume and to permit its standing upright with no further harm. This box may be covered with paper, cloth, or leather, the selection of material naturally being dependent on the binding of related volumes or the value and importance of the material thus protected.

*Supply* The various materials mentioned herein may be  
*houses* purchased from library supply and bookbinding supply houses. Paper, small cutlery, paste may probably be carried by the local stationer. Chemicals and oils can be got from or through the local chemist or druggist. For retail buying of book repair kits, binder's cloth, paste, glue, and general mending supplies, the following firms may be kept in mind:

Demco Library Supply Company, Madison, Wisconsin

Gaylord Brothers, Syracuse, New York

H. R. Hunting Company, Springfield, Massachusetts

## CHAPTER V

### The Treatment of Paper, Vellum, Etc.

TREATMENT of the paper stock is usually the first requirement in the repair or reconditioning of manuscripts or old books. Sometimes, to be sure, it may be the binding or cover, the ink, or the pigment in illumination or decoration that needs attention, but the chances are in favor of the paper's requiring aid and treatment first of all. If the paper is unbound and in form of loose leaves the methods of treatment and handling will be practically the same as in Chapter IV, except that more patience, skill, care and attention must be given. If the paper has to be handled in shape of a few leaves in a bound volume needing repair or mending a skilled workman may be able to handle them without rebinding the volume completely, but there is no doubt that better work can be done if the book can be taken out of its covers and if the sheets can be handled flat.

With the risk of the charge of repetition fully in mind let it be said that the same general principles govern here as in Chapter IV. Mending paper should

*Treatment  
of the  
paper stock*

*Paper for  
mending*

## The Care and Repair of Books

be of the same grade, thickness, and texture as the page to be repaired, or as near as is possible. Any binder with a plant of any age will usually have stored away a quantity of loose sheets of old paper of all sorts, held for just such uses as this. Thickness, weight, texture come first as specifications to be met. They are less simple to change than color and tint. With the first three granted or assured it usually is fairly simple to meet the problem of color or tint. Darkening may be secured in various ways, but bleaching is not so simple. With a solution of tea or coffee an experienced workman can darken a sheet to almost any tint demanded. If you watch him at work you will notice he first tries a sample bit or full sheet and gets it thoroughly dry before he steeps the working sheet. It is dangerous to accept a solution unless one has tested it under working conditions and is sure of the result, whether a solution of tea or a solution of a problem.

*Ethics of  
repair  
work*

Just when it is right to repair a tear or make a restoration so completely as to show no signs of repair or restoration is a question of ethics that must be passed on for each individual case. There is no general rule governing all instances. If the end and aim are deception, then the effort is indefensible. If it is

## The Treatment of Paper, Vellum, Etc.

merely an effort to return the page or sheet as nearly to its original condition as possible, then the effort is commendable. It all depends on the aim in view. Some collectors and booklovers insist on the repair work and restoration being performed in a way to render the page perfect but to show in plain and honest fashion just what had been done. Repair is honest, deceit is not.

Several varieties of Japanese tissue are suitable for mending torn pages. Pages with large tears, holes, missing parts may require extensive patching. Worm holes, similar perforations from any other cause may be filled in by means of a paste filler made of paper pulp or paper fluff and paste. This pulp or fluff may be got by scraping a sheet of the same paper stock with a sharp knife, scraping fluff from blotting paper, reducing paper to pulp by boiling. Add the paste to the pulp, and stain the mixture to match the stock to be repaired. Spread the original sheet out on a piece of plate glass, dampen it and fill the holes with the pulp, applying it with the blade of a small knife, smoothing it with a bone folder or similar instrument, placing it between wax boards for drying.

*Filling  
holes in  
paper*

When it comes to a question of cleaning paper re-

## The Care and Repair of Books

*Cleaning paper* member that the first qualifications are good common sense added to a knowledge of paper stock. Before beginning to clean paper stock a prudent workman will make a careful study to see how strong it is and how successfully it will probably withstand the rigors of cleaning. It's a really wise man who knows when to let well enough alone. Even a soft eraser may be too much for some weak fibred and brittle stocks.

*Rubber erasers* If the paper is reasonably strong several methods of cleaning lie open to choice, depending largely on the nature of the spots to be removed. Surface dirt, pencil and finger marks, soil that has stained the surface but not penetrated deep, will frequently yield to a soft rubber eraser, a sponge rubber, a piece of art gum, even a small lump of clean dough.

*Solvents* Benzene, benzole, gasolene are helpful in removing oil and grease stains. Saturate the spot with one of these solvents, place the sheet between blotters, and go over it with a hot iron, hot enough to remove the stain and solvent but not hot enough to burn. If the stain is old and the saturation heavy it may be well to soak the spot thoroughly in kerosene for several hours before using the benzene, benzole, or gasolene.



## The Treatment of Paper, Vellum, Etc.

Alcohol is excellent for removing iodine, mold, mildew stains.

All these solvents are harmless to paper stock. But they may dissolve not only the stains but the printing ink, causing it to run and give another and unexpected stain. A word of needless warning also cautions against using any of them near an open flame. Their fumes may be ignited several yards away from the flame. After using them open the windows and change the air.

*Warnings*

Good rag papers may be washed in a bath of soapy water, or may be cleaned by sponging them with a soap jelly, then removing the soap with a clean damp sponge. Take care to see that the soap is pure, free from scent or coloring materials, a good castile soap being safe.

*Washing  
of paper*

A few spots in a bound volume may be treated here and there, but if there are many it is better to take the book out of its binding. Recasing may call for more care and attention, but the result will probably be better if the sheets can be handled freely and be put to press by themselves, leaving those that need no treatment to rest in peace.

Coated paper, highly glazed, should never be touched by water, which will certainly dissolve the

## The Care and Repair of Books

surface and ruin the paper beyond possibility of repair.

*Sizing of paper* Most papers, except blotting paper and soft, high bulking book stock, are sized. Sometimes sizing is done in the beater before the paper is made, but in the better grade papers sizing is done after the sheet has taken shape. Size is any gelatinous substance, such as casein or starch or glue, that is added to the paper stock to glaze the surface, binding the fibres together, improving the surface, adding to the strength. With book and writing papers it is usually a good quality animal glue. Put a sheet of paper in a bath of water, or treat it with chemicals to wash or bleach it, and you will find that removing the stain or discoloration or dirt has likewise removed the original sizing material. The sheet is limp and soft, useless for its original purpose.

*Resizing* But, resizing will restore it. This, however, should be the last step in the process of restoration. All other things must have been cared for, nothing more to be done but returning the surface to its original condition. To make the size take one ounce of the best gelatine or one ounce of isinglass, and dissolve it in 32 ounces of water. Mild heating of the water will hasten the process. Reducing the amount of water

## The Treatment of Paper, Vellum, Etc.

will make the size stronger, but the heat should be applied gradually to prevent danger of burning the liquid and turning it brown.

If luck or skill has been with you there will be a clear liquid in the container. Strain this through a clean cloth into a shallow pan large enough to hold the sheets of paper about to be treated. Best results will follow if this shallow pan can rest above a gas flame or some other form of heat to keep its contents at about 125 degrees Fahrenheit.

And now comes the time for immersing the paper. But be sure to look at it carefully once more, to be sure it calls for no further attention, to be sure all dirt and pencil marks and finger prints have been removed. If not, sizing merely means fixing them. Some stains, however, will be removed in the warm bath, especially brown water stains.

Carefully put the sheet in the size bath, and then take it out, not too slowly, not too hastily. Put the sheets on top of one another, and when the whole book has been treated the pile of sheets should then be placed between backing boards and be put in a backing press to have the surplus liquid squeezed out into the pan placed below to catch the drip.

Then spread the sheets out on large, clean sheets

## The Care and Repair of Books

of paper, to dry. It means that care must be taken to prevent the sheets sticking together while in the press or while laid out to dry. With proper equipment it may be best to clip each sheet to a line and let it dry by hanging in the air at a convenient height. In either case dust and dirt must be kept from them. After drying they must be run through a mangle or press, then folded, and made ready for binding. If there are only a few sheets for treatment it may be sufficient to lay them between sheets of clean blotting paper, then ironing or pressing them when dry. But in all cases be sure they are quite dry before taking the next step.

*Foxing* Not infrequently on old paper, less commonly on modern stocks, one finds a dull rusty patch discoloring the page in annoying fashion. This is due to "foxing," the term going back to the rusty red of Reynard the Fox. Just what causes it is not certain. Perhaps a fungus growth in the sizing materials sets up decay closely akin to mold or mildew. Perhaps it may be charged to imperfect cleansing of the chemicals or to impurities in the water used in manufacture. Sometimes it may be removed by chemical treatment; sometimes caution suggests that with paper already so sadly weakened it may be better to

## The Treatment of Paper, Vellum, Etc.

accept the foxing than to run the risk of further weakening by treatment.

Bleaching of paper for removal of foxing and other stains may be done by several chemicals, all with the advantages and disadvantages of such treatment. The fly in the ointment appears in shape of the warning that many chemicals remove spots and also weaken the paper. Bleaching is perfectly possible, but it is recommended only when it will not do more harm than good.

Excellent results for bleaching may be secured by the use of potassium permanganate and potassium metabisulphite, when in the hands of competent and intelligent workmen. Three shallow trays are needed, one filled with permanganate, the second with water, the third with the metabisulphite, each of the potassium compounds diluted to the strength of one ounce to sixteen ounces of water. Put the paper in the permanganate solution for a short time, say thirty to sixty seconds. The sheet will turn a deep, purplish brown in this staining solution. Lay it next in the clear water and wash off the permanganate. Then comes the turn of the potassium metabisulphite, and in it the sheet will turn white almost instantly. Leave it in this pan until all the stains and spots disappear,

*Bleaching*

*Bleaching  
by  
potassium*



## The Care and Repair of Books

and then put it into running water to wash till all traces of the chemicals have been completely removed. Let it dry between blotters, and then put it to press to remove wrinkles.

*Other bleaches* Now and then a stain will greet the workman with refusal to disappear in the metabisulphite solution. In such a case wash off the metabisulphite with clear water, put the sheet in a pan containing a solution of potassium ferricyanide of the same 1:16 strength. If it does not disappear quickly the case is almost hopeless. But another attack may be made with a hydrochloric acid solution of the same strength, after having washed off the previous chemicals. If the spot still persists it may be written down as practically removal proof.

*Toning down to neutral shade* This bleaching leaves the paper snow white, and if the sheet is to be toned down to what is called a neutral shade it may be darkened at will by soaking once more, this time in a water bath colored by a solution of tea or coffee or a brown aniline dye. This stain may also be mixed with the sizing liquid. Prudence and forethought suggest that it may be well to test the strength beforehand by dipping and drying a small test sheet as a sample to make sure the right shade has been secured.



## The Treatment of Paper, Vellum, Etc.

Permanganate is, to be sure, not the only treatment. Many other formulæ may be brought forward, some with a record of success and some with less fortunate histories. Oxalic acid, javelle water (chlorinated potash), ammonia, hydrogen peroxide, sulphite of soda, bicarbonate of soda, and other solutions and combinations all have their advocates. All offer promising opportunities for the workman with a bent toward experimenting.

*Other  
formulæ*

With hydrogen peroxide it is best to take a shallow pan and fill it with liquid plaster of Paris. When this sets and hardens saturate the slab of plaster with hydrogen peroxide, and lay on it for several hours the print to be treated, face down. If the effort is successful and the spots disappear the sheet must then be washed, dried, pressed. If the spots refuse to budge perhaps a stronger solution may have better luck; perhaps a mixture of peroxide and ammonia or alcohol may succeed. These combinations seem less reliable than the potassium treatment, but there is no certainty that the various results may not be due more to varying skill of the workman than to the chemicals themselves. Perhaps it is a matter of opinion, perhaps not.

*Hydrogen  
peroxide*

When hydrochloric acid is used the acid must be

## The Care and Repair of Books

*Acids and alkalis* poured into the water, not the water into the liquid. If the latter is done there is danger that the liquid may splutter and splash out of the container. When an acid is used for the bleach the paper should have an alkali bath as a neutralizer. After javelle water the paper should be washed in a solution of sulphate of soda. If hydrochloric acid is used the afterwash should be bicarbonate of soda.

This is all well enough as a statement of ideal, but there is danger of failure unless one brings to the effort satisfactory training in chemistry. The solutions must be perfectly balanced to insure this neutralization, and in this as in other things success is largely a result of ceaseless striving. Be prepared to make many experiments with paper of no value before trying to bleach important documents.

*Warnings* With single sheets in a book it may be best to cut them out, bleach, wash, tint, and remount them on a stub left for the purpose. In such cases it is of course perfectly obvious what has happened, and there is of course also the danger of failing to secure an even tint as compared with the rest of the volume. To insure uniformity, and to work more expeditiously if there are many sheets calling for treatment, it may be most convenient to take the whole volume out of

## The Treatment of Paper, Vellum, Etc.

the covers, treat all sheets, wash, dry, press, resew, recover.

Bear in mind also that this attack by chemicals, this washing and rewashing, this bleaching and tinting may be safe with paper of undoubted strength, but it is weakening even for the best, and certainly is dangerous for stocks with fibres affected by attacks of one kind or another. The experienced eye will decide not infrequently that it will be more satisfactory to accept the sheet with the stain and with a known and certain strength rather than to succeed in removing the stain and at the same time secure dangerous weakening of the fibres. Occasionally decay has gone so far that covering with silk or Japanese tissue paper offers the only hope of preservation even with the stain left in all its rawness.

Remember too that treatment of black and white prints (whether done by ordinary typography or by engraving or etching processes) is one thing and treatment of colored prints decidedly another. Color prints made with ordinary fast colors, aquatints, modern offset color prints, and all ordinary black letter prints and engravings may be treated with potassium permanganate and potassium metabisulphite with every hope of success if the work is done

*Dangers of  
weakening*

*Treatment  
of color  
prints*

## The Care and Repair of Books

with ordinary care and attention. Such prints may be cleaned and brightened, may have all traces of stains removed from the paper without damage to the color. But danger lies in the face of the man trying to treat in this way paper bearing water colors, or sheets printed with ink of fugitive colors, or sheets with highly coated surfaces. The water colors will run, the fugitive colored inks will disappear or bleach, and the starch and clay and size of the highly coated surfaces will soften and stick together or the surface coating will wash off completely as soon as the sheet is given its water bath. Even with black and white prints a knowledge of ink and color is advisable. Bleaching tends to weaken ink and color and paper stock. Modern carbon black inks are acid proof, to be sure, but even with them there is constant and insistent call for attention and alertness. An open mind and a willingness to experiment will well repay all efforts they demand. In case of doubt or question it surely is simple to find a piece of paper similar to if not identical with the one in question, and test and try it before giving the primary sheet its irrevocable plunge.

Sometimes the printed page suffers an accident that dims the text by rubbing, chemical action, or

## The Treatment of Paper, Vellum, Etc.

various other causes. Restoration is not impossible for the steady hand guided by an experienced eye. The obvious means is a bottle of India ink and a draftsman's pen. Printing types may also be used. For this latter process select a face as near the original as possible. Spread a bit of printer's ink on a sheet of glass or other smooth surface, by means of a brayer or printer's hand inking roller. Dampen the paper slightly. Ink the type by means of the brayer, getting it on not too much nor too little. Then press the type down on the paper. Two or three "warming up" exercises on specimens where mistakes are not vital will help insure success on the important sheet where an error is unforgiveable. Be sure, however, to experiment with a sheet of the same general character as the original stock.

When rubricated initials fade restoration is possible by means of ink of proper shade and material. In general a good oil paint applied by a fine camel's hair brush will give satisfaction. The treated page should dry thoroughly before being handled. Rubrication or illumination done by oil paint or by printer's ink necessarily calls for oil color or printer's ink restoration; where the decoration is in wash or water colors restoration must be in the same medium. It is

*Restoring  
lettering*

*Restora-  
tion of  
rubricated  
letters*



## The Care and Repair of Books

surely needless to sound a warning against letting any one but an artist and workman of unquestioned ability undertake a task of this kind.

*Vellum and parchment*      Parchment and vellum present decided difficulties in handling. Made from the skin of calves or sheep they change almost as rapidly and widely as the thermometer. That statement is exaggerated, as a matter of fact, but there is no doubt about the trouble they make while kept under modern conditions.

*Preparation of skin for writing*      Skin has been used for writing materials from an early date. It comes down to us usually in form of a volume or codex, sometimes also as the binding for such a volume, more rarely in the primitive form of a roll. The skin was limed, shaved, washed, stretched, scraped, rubbed smooth with pumice stone, and then turned over to the scribe. Skins from still-born calves were usually selected for the finer sheets. Those from the older animals were usually so tough they could be put to better use as bindings than as sheets for the written message.

Vellum in any form is affected by heat and moisture more than paper. It is inclined to stretch, shrink, wrinkle, cockle, warp as the surrounding air grows more or less moist or humid. This explains the straps or thongs or clasps found so frequently on old parch-



## The Treatment of Paper, Vellum, Etc.

ment bindings. But even such fastenings fail to keep the cover flat and straight, and for shelving under modern conditions better results will follow the use of a slip case than thongs or clasps. The case should be tight enough to keep the volume under constant pressure, loose enough to permit the book to be put into it or taken out without harm.

Old vellum is frequently yellow or cream in tint, sometimes just cream enough to be altogether attractive, but not infrequently so near brown as to render the writing difficult to read. It may be bleached, but bleaching should be chosen only as a last resort, the burden of recommendation for such action being serious and demanding unquestionable justification. The danger of making the ink run is something to be borne in mind, for most specimens calling for attention will probably be manuscripts done with writing inks rather than printed pages, and some writing inks are less permanent than most printing inks.

Far better to try first to clean the sheet by sponging with a lather made from a good soap, free from acid or alkali, the lather made with as little water as possible. After sponging carefully wipe it dry, put blotting paper on each side, place it in press or under weights until thoroughly dry. A soft rubber eraser,

*Bleaching  
vellum*

*Cleaning  
vellum*

## The Care and Repair of Books

alcohol, benzene are other cleansing means to fall back on as need arises.

*Smoothing  
wrinkled  
vellum*

When it comes to straightening vellum leaves that have bent or twisted or cockled the first thing to do is to moisten them, but real care must be taken to see that water does not come in direct contact with the sheet. This is particularly important in the case of illuminated manuscripts. Water may be applied directly, to be sure, but there is danger then of starting the ink to run or danger of removing it. A safer way is to apply this moisture by means of a humidifier or a box made in a way to hold moistening pans or to permit safe introduction of steam.

*Straighten-  
ing single  
sheets of  
vellum*

If the book can be taken apart the problem is simpler than if it must be met by treating the bound volume. With single sheets it is simple to make a frame of wood, slightly larger than the sheets to be treated. Then attach clips to the sheet, with strings attached to weights. The sheet can be so adjusted that there will be an even pull in all directions, and the moisture will permit it to be flattened evenly. Be sure it is completely dry before removing the clips and strings. The drying should be gradual, and sometimes it may be well to apply artificial heat if the heat can be kept well under control. Haste will do more

## The Treatment of Paper, Vellum, Etc.

damage than good here. Remember that parchment comes from the East, and remember the word of advice about trying to hurry the East. It holds good here without question.

Sometimes vellum may be softened by application of steam, but live steam must never come in contact with the skin.

Be sure the sheet is perfectly dry when taken from the press. Otherwise you have the work to do over again, for warping and cockling are almost inevitable unless the drying was complete.

After the vellum has been washed with soap and water it will naturally be somewhat softer, and before it becomes brittle and hard again it should be given two or three applications of neat's foot oil and lanolin, rubbed well into the skin. This will keep the skin in good condition and help render it less affected by moisture or dryness in the air.

Pasting an extra sheet of paper inside each cover often helps correct badly warped vellum covers. This tends to draw the covers inward, and to keep the boards flat by counteracting the outward pull of the vellum.

Manuscripts on leather that is decidedly neither vellum nor parchment sometimes come to attention

*Oil for  
vellum*

*Warped  
vellum  
covers*

## The Care and Repair of Books

*Other leather manuscripts* in shape of drawings on skins made by American Indians or other primitive people. They need about the same kind of treatment as other skins, moistening to flatten under pressure, application of neat's foot oil and lanolin to keep soft and pliable, sewing tears to prevent further running, or patching with fresh skins to fill holes or straighten edges. Skins as nearly the color and texture of the original should be chosen, to make an obvious remark, the edges shaved as the piece is cut to the size of the hole to be filled, binding done by means of any good leather cement. Need for care of this kind will come so seldom to the average librarian or collector or binder that attention to individual cases may well be left to advice of specialists when need arises. But, to repeat once more, the same general principles governing attention to vellum and parchment and leather bindings will govern here.

*Papyrus* Papyrus is the name applied to the writing material used by the ancient Egyptians, the Greeks, and the Romans. It was prepared by cutting longitudinal strips of fibres from the papyrus plant, laying them across one another in two layers, soaking them in water, and pressing them into a smooth, even surface. There was enough natural glutinous matter in

## The Treatment of Paper, Vellum, Etc.

the fibres to cause them to adhere closely when pressed or beaten dry; some people credited this adhesion to the peculiar qualities of the water of the Nile. After they came from the press they were smoothed with pumice stone or some other abrasive.

The ink used on them was probably made from water, glue, lamp black or carbon. This must constantly be borne in mind, as there is danger of seeing the ink run if the sheet is carelessly soaked in water.

Papyrus sheets come in various sizes and in all sorts of conditions. According to Pliny "There is a great difference in breadth of the various kinds of paper. That of the best quality is thirteen fingers wide, while the hieratic is two fingers less. The Fan-niana is ten fingers wide, and that known as 'amphia-theatrica' one less. The Saitis is of still smaller breadth, indeed it is not so wide as the mallet with which the paper is beaten; and the emporetica is particularly narrow, being not more than six fingers in breadth." (Natural History, book 13, chapter 24.)

*Papyrus  
sheets*

They were usually made into rolls about twenty or thirty feet long, but sometimes were used as single sheets about the size of one's palm. They come to us today in both forms, and to meet modern conditions the rolls should be cut into convenient sections and



## The Care and Repair of Books

these sections, as well as single isolated sheets, should be protected by glass.

*Straightening papyrus sheets* Many of these sheets are sadly wrinkled and creased, brittle and dry, breaking at the slightest attempt to flex or bend or fold. The first requirements for straightening them and putting them into condition for reading are trained hands, intelligent eyes, common sense, an alert mind. To these immaterial things may be added such equipment as a sheet of plate glass, some sponges, a water bowl, some small brushes, blotters, flat bladed knives, and at least one knife with a pointed blade.

First see that the sheet of glass is clean, absolutely clean. Then wash it off with benzene. This will leave a slight film of oil on the glass, preventing adhesion. Then dampen it with a sponge and water. Spread a piece of fine silk gauze smoothly over the glass. Put the papyrus on the gauze and wet it with sponge and water until it becomes soft and flexible. Flatten out the wrinkles by stretching and pressing. The point of knife or a small brush may help rearrangement of fibres formerly fixed discouragingly out of place. Turning back portions folded over may occasionally bring the thrill of revealing part of the text hitherto hidden and unknown.



## The Treatment of Paper, Vellum, Etc.

More water will bring out dried mud and dirt, but this water must be removed quickly by soaking it up with the sponge. When the necessary folding and flattening and smoothing have been finished, blot off the surplus water, and lift the sheet off the glass by means of the silk gauze, which will thus support the papyrus and make removal more safe and easy than without it.

Put the papyrus face down on a blotter and strip off the gauze. Let it dry partially and then put it to press. If pressed while it is too dry there is danger of blotting off the ink. If it gets too dry before pressing it will wrinkle and cockle again.

When both sides of the sheet bear writing two glasses may be used, both prepared in the same manner with benzene and gauze. Finish the first side of the papyrus sheet, strip the sheet off the glass, lay it face down on the second sheet of gauze and glass. After it has been treated, washed, flattened, finished, strip it and place it on a blotter for drying.

When dry the sheet should be perfectly flat, but it will not stay flat unless it is protected, something best secured by laying it between two sheets of glass and binding them by a tape *passe partout* or a wooden frame. If there is no writing on the back, or

## The Care and Repair of Books

no other objection, it may be well to mount the papyrus on a good quality of picture mount board and frame it under glass. Sometimes it may call for covering with silk before putting under the glass.

In all this it is experience and common sense that insure success much more than any formal set of rules to govern details of method and procedure. A binder competent to do work of this kind will succeed if he is grounded in the fundamental principles of his work and supplements them by an alert mind and an active interest in accomplishing the unusual, no matter whether he has been given rules or not. No need to tell him to try his first ideas on pieces that do not count, rather than begin with an attack on papyrus of first importance.

*Oriental  
manu-  
scripts* Manuscripts from the farther East, China, Japan, and India appear on paper, palm leaves, and occasionally on leather. Treatment of the paper stock is governed by the same principles controlling paper made in the western world; earlier specimens are all hand made and are usually better than the machine made samples of more recent years. Technique of handling them differs only as the surface and foundation stock differs from more common paper. So too with writing on leather. Leather is leather, and

## The Treatment of Paper, Vellum, Etc.

its care and treatment are the same whether it was tanned or prepared east of the 180th meridian or west of it.

Manuscripts on palm leaves demand treatment rather infrequently. When holes in them must be filled the task is more for the cabinet maker skilled in veneer work than for the ordinary binder. So too manuscripts from the Pacific Islands call for such special attention as to insist on treatment and care by workmen of such special skill and experience as to need no help from a book like this. Each case must be handled as its demands are studied. Holes must be filled by something as nearly like the original as possible. Tears must be controlled by some safe adhesive. Protection must be assured by restoring the covering wrapper, by making a new frame, by taking such steps as the case seems to call for. If the workman is intelligent and skilled and honest he will know how far his previous experience will carry him, and likewise will know at what stage he must call for help and advice. If he is not of this type the work should not be put into his hands.

*Palm leaf  
manu-  
scripts*

## CHAPTER VI

### The Care of Leather Bindings

*Leather as  
binding  
material*

OF all bookbinding materials leather comes nearest to being ideal. It is pliable, can be worked to advantage by both forwarder and finisher, takes tooling and gold admirably, is good to look upon, is delightful to handle. Till recently it was the most lasting material known for this purpose and was always specified when books were to be bound in the best manner possible.

*Modern  
tanning*

The tanner, however, yielded to the insistent cry of the customer for more speedy delivery, renounced time honored traditional methods, rushed the hides through the vats, and handed the binder a skin inferior in every way—save quickness of tanning—to those produced with less haste. The last fifty years have seen the worst of this practice, and it is safe to say that few books bound with leather tanned during this period now have their leather in good condition, at least in this country. Many recently tanned skins show deterioration within five to ten years, and few tanned within the last half century can com-

## The Care of Leather Bindings

pare with older leather. Now and then by careful shopping one may find well tanned skins, acid free and certain of long service, but tanners with pride enough in their calling to turn out skins warranted to last do not stand on every corner.

It is the introduction of sulphuric and other acids into tanning processes that must bear much of the blame for this state of affairs. Decay is helped also by the infusion of acids and other bleaching agents used to produce even shades of color.

*Acids in  
tanning*

A faint ray of hope is suggested by the belief that some competent judges trust chrome tanned leather may prove as lasting as that turned out by old fashioned vegetable tanning, but so far little more can be said than that hopes are encouraging but lack complete confirmation.

*Chrome  
tanning*

It is scarcely fair, however, to lay all the blame on the tanner. He certainly has much to answer for, but he might very properly ask if the most unmitigated optimist could expect well tanned skins to overcome the gas charged atmosphere of our modern cities. There is no doubt that the high sulphuric acid content of the typical industrial city has much responsibility for decay of leather bindings. If the skin is subjected to dampness the danger of mildew is always

*Gas  
charged air*

## The Care and Repair of Books

present. Direct sunlight is harmful also, as is storage in rooms too warm and dry. The binder can not escape unscathed if he wet the leather too much or stretched it too much when covering his boards, or if the finisher used oxalic acid or vinegar.

*Air con-*  
*ditioning* Book owners and librarians may mitigate some of these harmful effects if they do not remove them entirely, by control of ventilation and humidity. Clean fresh air, not too hot, not too moist, not too dry, should be given constantly. Books on the upper shelves should be watched particularly, for they usually suffer most from excessive dryness and from accumulation of harmful gases.

*Leather*  
*dressings* Application of certain dressings will lessen the harmful effects of modern conditions on leather bindings. Some of these dressings are mentioned below. How often they should be applied will depend on circumstances. There is no general and universal rule of faith and practice, but a moderate amount of attention joined to a bit of common sense will soon show when leather begins to dry off, to crack at the edges or corners or hinges. Of course the remedy should be applied before necessity arises, but it is given to few of us to be foresighted enough to anticipate trouble of this kind. In general it may



## The Care of Leather Bindings

be safe to suggest once a year or thereabouts for the ordinary collection in the modern building in the average American city. When conditions change to extreme north or south, to very damp or very dry places, to high altitudes, to the tropics, or to other unusual situations the needs become so far removed from the average as to call for special attention.

Here are formulæ for several dressings all of which have been proven helpful for leather:

Take four parts of lanolin of about the consistency of lard, and warm it slowly until it becomes fluid or free running. To this add six parts of neat's foot oil (pure, filtered, wholly neutral), mixing the two thoroughly. When cool, apply the mixture with a flat varnish brush of proper size, or a soft cloth or pad. Let the books stand for a few hours or overnight until the oil is absorbed. When dry, rub with a soft cloth. If more polish is required apply a small quantity of castor oil with a soft cloth or pad, and when it is dry rub with a chamois or sheep's wool polisher.

*Lanolin  
and oil  
dressing*

Take care to keep the oil away from the paper of the book or from cloth to be used in binding. Experienced workers frequently hold the book in the left hand and apply oil and cloths with the right. It

## The Care and Repair of Books

is certainly needless to remark that large volumes should be placed firmly on the table and should receive particular attention to see that no unexpected mishap marks the treatment.

Newly bound books may be treated on receipt, with a second treatment six months later, and a third in about a year if conditions seem normal and average.

Lanolin is prepared from sheep's wool. It is light yellow in color and it absorbs water readily. It is used generally as a base for ointments and cosmetics, and does not become rancid. Neat's foot oil is extracted from the feet, bones, and hide of neat cattle. It is pale yellow in color, consists mostly of olein, and is used as a fine lubricant and as a leather dressing. Castor oil comes from the seed of castor oil beans. When fresh it is inodorous, but it becomes rancid on exposure to the air.

In 1926 the Bureau of Chemistry of the United States Department of Agriculture suggested the following composition (all parts by weight):

Castile soap .....	3 per cent.
Neat's foot oil, 20 per cent. cold test, pure	25 per cent.
Tallow .....	10 per cent.

## The Care of Leather Bindings

Turpentine, pure gum .....	12 per cent.
Water, distilled, or clean rain water ..	50 per cent.

Dissolve the soap in the water by heating on a steam bath or in a double boiler. Melt the tallow in the neat's foot oil by heating in the same way. While both solutions are hot pour the soap solution in a thin stream into the tallow and oil mixture, stirring thoroughly until a homogeneous milky-white emulsion results. After this cools to room temperature add the turpentine and stir until thoroughly mixed. Keep in a well stoppered bottle or can. Shake before using, and apply in the same way as the oil dressing.

Here are five formulæ developed by Dr. Fletcher P. Veitch, principal chemist in charge of the Industrial Foreign Products Division of the Department of Agriculture at Washington, associated with Mr. R. W. Frey of the same Department, in reply to a request from the Library of Congress in 1929:

### Number 1:

	per cent.
Lanolin, anhydrous, U.S.P. ....	50
Japan wax .....	20
Sodium stearate .....	5
Sperm oil .....	25

## The Care and Repair of Books

### Number 2: .....

Lanolin, anhydrous, U.S.P. ....	50
Japan wax .....	5
Castor oil, U.S.P. ....	40
Sodium stearate .....	5

### Number 3:

Lanolin, anhydrous, U.S.P. ....	50
Japan wax .....	10
Neat's foot oil, 20 per cent. cold test, pure ..	35
Sodium stearate .....	5

### Number 4:

Lanolin, anhydrous, U.S.P. ....	30
Japan wax .....	5
Castor oil, U.S.P. ....	12
Sodium stearate .....	3
Water, distilled .....	50

### Number 5:

Lanolin, anhydrous, U.S.P. ....	17.5
Japan wax .....	10.0
Neat's foot oil, 20 per cent. cold test, pure ..	25.0
Sodium stearate .....	2.5
Water, distilled .....	45.0

## The Care of Leather Bindings

Unless the leather is much worn any of the five may be used first as a cleanser and then as a dressing to follow. Treated books should be allowed to stand 24 hours after the dressing has been thoroughly worked into the leather.

Of the five the Library of Congress found the fourth best suited to its needs.

A formula developed for the British Museum stands as follows:

Lanolin, anhydrous .....	7 oz. (avoir.)
Beeswax .....	1½ oz. "
Cedarwood oil .....	1 oz. (fluid)
Hexane .....	11 oz. "

*British  
Museum  
dressing*

Dissolve the wax in the hexane in a warm place, taking care to keep it away from naked lights, as hexane is volatile and easily inflammable. Add the cedarwood oil, and then lanolin, which should be previously softened by warming. The mixture must be thoroughly shaken before using.

"The chief reasons for combining these ingredients in this leather dressing may be briefly stated as follows. Lanolin is an animal fat which is very easily absorbed by leather and does not become rancid. At ordinary temperatures it is in the form

## The Care and Repair of Books

of a thick grease, and to use it thus would be to get uneven results and unduly strain the leather binding. A little wax is added to assist in polishing and to provide a thin surface film which, in the treated binding, reinforces any powdery or cracked portions of the leather and provides a protective 'skin' of considerable importance, particularly in the case of vellum bindings. The cedarwood oil, in addition to its well-known qualities as a preservative, is of value in forming a bond of union between the lanolin and wax in the leather, and hexane is chosen as a convenient 'thinner' as it readily dissolves beeswax.

"The method of applying the mixture is as follows: First the bindings are washed in the usual manner and set out to dry in a warm room for two or three days, and then the leather dressing is well rubbed in. The leather will now feel greasy to the touch, but after standing for forty-eight hours it will be found that this lanolin has penetrated and the binding can be easily polished. This operation leaves on the surface a shiny 'skin' which shows the grain of the leather to the best advantage. It is not in any way a sticky or resinous surface after polishing, and the general effect of the treatment is to soften the leather and prevent it from drying up.



## The Care of Leather Bindings

"This mixture forms a cheap and effective dressing for all kinds of leather and vellum." (British Museum Quarterly, January, 1928. v. 2, pp. 77-78.)

Oil of egg has also been used with success. It is obtained by extracting yolks with ether or chloroform, and is used also in preparation of ointments and emulsions, and in tempera painting. Leather is sometimes treated with "eggio," prepared from eggs preserved in the liquid state by adding salt and borax. (Thorpe's "Dictionary of Applied Chemistry," 1921. v. 2, p. 616.) When oil of egg is used it is subsequently followed by a dressing of beeswax to give a polish by rubbing vigorously with a soft cloth. Some libraries use a furniture polish put up in England, and at least one individual comes to mind who swears by his saddle dressing as equally good for his leather bindings. Neat's foot oil surely serves many purposes.

*Oil of egg  
dressing*

From time to time other formulæ have been brought forward, and all deserve thoughtful consideration. Some are described as secret preparations, so carefully compounded as to urge the fortunate discoverer to keep the mystery sealed from curious or unsympathetic or unappreciative eyes. The temptation is strong to ask if you have sufficient ground for

*Secret  
prepara-  
tions*

## The Care and Repair of Books

confidence that when the seer was granted insight into the mysteries assurance was also given that no harmful ingredient was thoughtlessly or inadvertently added. "Caveat emptor" holds good in many fields. Some of these "secret" preparations have been analyzed and found to contain harmless ingredients, but priced much higher than the component parts could have been bought for in the open market. Of course the seller deserved remuneration for time and trouble in combining the materials, in selecting an attractive container, and in evolving an enticing name, but whether this cost was reasonable or excessive may be left as a matter of opinion. Common sense, however, asks why in heaven's name one should choose a "secret" formula when harmless and helpful ingredients, in covenants openly arrived at, lie freely at hand.

*Mineral oil  
and leather*

In all the formulæ set forth above all the oils and greases—with but one exception—are either animal or vegetable. Vaseline and other mineral oil compounds have their earnest advocates, but some of us believe that the less mineral oils are used on leather the better it is for the leather. Ask any machinist what effect mineral oil has on leather driving belts, and he will tell you that it causes the belt to crack

## The Care of Leather Bindings

and disintegrate, in direct contrast to the effect of animal or vegetable oils. Bookbinders will generally give the same testimony as to the relative effects of animal or vegetable oils as contrasted with mineral oils, so far as leather bindings are concerned. Lamb's "Leather Dressing" (3d edition, 1925, p. 256) says "Mineral oils are advantageous when used for lubricating purposes; they are useful in currying and for oiling-off of various leathers; they, however, do not feed and lubricate the fibers of leather as effectually as animal or vegetable oils."

Some years ago the binders in The New York Public Library realized how conflicting were the pieces of information and advice they were able to secure as to treatment of leather, and they set out to experiment and observe for themselves. Every solution or preparation that came to attention or could be found by diligent search was tried, and careful notes were taken of the results. Samples for testing were taken from levant, morocco, pig skin, calf, cow, sheep, tanned in this country and in England, France, Germany. Swatches from designated parts of each hide were exposed to gas light and gas fumes in a chamber specially constructed for the purpose. Some were exposed to sunlight and to air under glass,

*Acid effects  
on leather*

## The Care and Repair of Books

and others to direct sunlight and unprotected city air. Some were treated with various preservatives and some were left untreated.

The experiments continued for many months, each particular exposure being at least 2,500 hours. At the end all the samples, treated and untreated, exposed and unexposed, were sent to the Bureau of Standards in Washington. Study and examination there showed that all skins treated with any preparation that came in the class of those mentioned with approval above were benefited, even specimens knowingly selected as acid tanned. Untreated skins deteriorated obviously, some showing practically complete disintegration. Treated specimens from the same skins gave strength tests at the end higher than in the beginning.

Five samples of one leather, a full chrome tanned calf skin that was not a book binding leather, were included. These withstood the action of gas fumes markedly better than any other sample, which seems to indicate that the substitution of chrome for vegetable tanning may solve the problem of permanence for bookbinding leather. Absolute proof, however, waits for further and more exacting testings.

The general experiment showed conclusively that acid tanned leather deteriorated when exposed to

## The Care of Leather Bindings

heat and to gas laden air, acid free leather suffered less. Both kinds suffered when exposed to noxious gases, acid free leathers showing greater resistance. Both kinds showed improvement when treated with preservatives. The test was scarcely long enough or comprehensive enough to demonstrate absolute superiority of one method of tanning as compared with all the others.

It needs no ghost come from heaven, however, to say that treatment of leather bound books should begin when the leather is new, with its life and strength unimpaired. Treatment will help leather resist the constant attacks given by its environment. Treatment will not help leather when the stock is thoroughly dried out or infected with rot or red rust. There the case is hopeless. Somewhere between the two extremes appears the condition when treatment will effectually restore fading life, or the condition when decline has begun but the decay will be lessened by treatment.

*Treatment  
should be  
frequent*

## CHAPTER VII

### The Treatment of Cloth Bindings

*Colored  
bindings*

COLOR has of late swept into the world of book bindings just as emphatically as it has taken hold of the bathroom or the kitchen or any other part of the house. Not so long ago book coverings were uniform and sombre in that uniformity. Here and there a library would bind one class of books in cloth of one color and another in a different color, but in every case every book in the class was in the same color and every specimen of color was uniform and sedate. No jazz there. But within a few short years book covers have yielded to this color advance. Publishers have vied with one another to find striking and attractive color effects, and the makers of binder's cloth have been as successful in selling these rainbow hued products to the binders for repair work as for original edition work. And now the librarian may make choice of brilliant colors, pastel shades, embossed patterns, cloths with two tone effects.

No doubt as to the bright and cheerful effects of the shelves of new books, and all is equally bright



## The Treatment of Cloth Bindings

and cheerful in the heart of the librarian until the books have circulated a few times and have taken their toll of the grime on hands that fondled them and the dirt on tables that held them. If not worn enough to call for rebinding could they be cleaned or freshened up?

If they were in artificial leather (usually cloth colored and surfaced to look like leather) or in the waterproofed buckrams the problem was simple. Dirt on such bindings responded readily to a cloth slightly moistened with nothing but water. Life is not so simple, however, and soon the binders began to complain that these artificial leathers and waterproofed buckrams did not take gold leaf easily and offered trouble when it came to pasting down the end papers. The gold refused to stick, and sometimes it came off after the binder had let the run pass on as a satisfactory bit of gold lettering or decorating. It meant an increase in cost of binding when an increase in amount of care and attention was demanded from the binder.

*Color in  
artificial  
leather*

To provide bindings that could be cleaned some binders choose to stick to the old fashioned book cloths, and varnish or lacquer them before putting them in circulation. Good book varnishes or book

*Book  
varnishes  
and  
lacquers*

## The Care and Repair of Books

lacquers can be had at any bookbinding supply house at moderate cost and in containers of sufficiently varied sizes to suit the needs of any customer. These varnishes or lacquers can be applied with a small piece of cotton, a brush, or if necessary with an air spray. The latter calls not only for power to run the blower, but also for space to house the equipment, and for an exhaust to outer air. Large plants can use this power spray with advantage, but for the smaller establishment hand work is usually sufficient.

Varnishing or lacquering a book tends to make the covers waterproof, and covers so treated may be cleaned with a damp cloth. Water should not be used on regular book cloths unless they are protected in some way. If not they will certainly give up finish, filler, color, when water is applied.

Often a piece of art gum or a soft rubber eraser will prove a great help in cleaning books soiled by ordinary handling. Grease spots and deep seated grime may sometimes be removed by benzene or benzole. The restoration of stained or faded book cloth is considered on page 58 of Chapter IV.

Would that all were agreed as to recognition of the perfect, non-soilable book cloth, bright and cheerful to look upon, happily responsive to hands of for-

## The Treatment of Cloth Bindings

warder and finisher, easily cleaned when its non-soilable surface is showing just the suggestion of taint. The manufacturers may honestly believe their next effort will solve the problem, but those of us who watch books struggle with the hands of their readers and users are inclined to wait just a bit longer before going quite that far.

## CHAPTER VIII

### Some Other Books

**H**ERE is a list of some other books on this subject. It is not a "bibliography," makes no pretence to completeness, but does represent an effort to set forth some of the important works in this field that have come to mind during the more than a few years the compilers have given thought to the problems set forth in the preceding pages. Almost boundless opportunities of increasing the list are open to the ardent soul who wishes to dig deeper into the volumes on the making of books, paper, leather, and related topics.

---

A D A M, Paul. Das sinngemässe Restaurieren alter Einbände. (Zeitschrift für Bücherfreunde. Jhrg. 7, p. 499-506. Bielefeld, 1904.)

A D A M, Paul. Das Restaurieren alter Bücher; Wiederherstellungsarbeiten an alten Büchern, Einbänden, auch Manuskripten sowie Ausführungen über das notwendige Verständnis für die Technik des Buches zur Beurteilung von Zeit und Herkunft

## Some Other Books

alter Einbände. Halle, Saale: W. Knapp, 1927. 28 p. 8°.

AMERICAN LIBRARY ASSOCIATION. Care and binding of books and magazines. By A. L. A. Committee on bookbinding, Mary E. Wheelock, chairman. Chicago: American Library Association, 1928. 2 p. l., 3-60 p. 8°.

ARNSBERGER & RHEINBOLDT, Offenbach a.M. Wissenswertes über die verschiedenen Sorten Leder für Bucheinbände; ihre Herkunft, Gerbung, Färbung, Narbung, Haltbarkeit u. Verwendung. Offenbach a.M.: Selbstverlag, 1928. 45 p. 8°.

BEAUFORT, Thomas Richard. Pictures and how to clean them; to which are added notes on things useful in restoration work. London: J. Lane, 1926. xi, 202 p. 12°.

BLADES, William. The enemies of books. London: Trübner & Co., 1880. xiii, 110 p. 8°.

BLADES, William. The enemies of books. London: Trübner & Co., 1880. 2. ed. xiii (3), 114 (2) p., 5 pl. 8°.

BLADES, William. The enemies of books. London: Trübner & Co., 1881. 3. ed. xiii, 1 l., 114 p., 7 pl. 8°.

## The Care and Repair of Books

B L A D E S, William. The enemies of books. Revised and enlarged by the author. New York: A. C. Armstrong & Son, 1888. xiii, 1 l., 165 p., 1 l., 6 pl. 8°. (The book-lover's library.)

B L A D E S, William. The enemies of books. With a preface by Richard Garnett. Chicago: A. C. McClurg & Co., 1896. xviii, 151 p., 9 pl. 8°.

B L A D E S, William. The enemies of books. Revised and enlarged by the author. London: E. Stock, 1902. xi, 155 (1) p. 8°. (The book-lover's library.)

B O N N A R D O T, Alfred. De la réparation des vieilles reliures. Complément de l'essai sur l'art de restaurer les estampes et les livres, suivi d'une dissertation sur les moyens d'obtenir des duplicata des manuscrits. Paris: Castel, 1858. 70 p., 1 l. 12°.

B O N N A R D O T, Alfred. Essai sur l'art de restaurer les estampes et les livres, ou, Traité sur les meilleurs procédés pour blanchir, détacher, décolorier, réparer et conserver les estampes, livres et dessins. . . . Suivi d'un exposé des divers systèmes de reproduction des anciennes estampes et des livres rares. Paris: Caste, 1858. 2. ed. rev. and enl. viii, 353 p. 12°.

B O N N A R D O T, Alfred. See also Buck, Mitchell Starrett.



## Some Other Books

B O W K E R, Roy Clement, and M. N. V. Geib. Comparative durability of chrome and vegetable tanned leathers. Washington: Government Printing Office, 1925. 1 p. l., 267-286 p. 8°. (U. S. Bureau of Standards. Technologic papers, no. 286.)

BRITISH MUSEUM. See Plenderleith, H. J. See also: Great Britain.—Department of Scientific and Industrial Research.

B R O W N, Margaret Wright. Mending and repair of books. Chicago: American Library Association Publishing Board, 1910. 22 p. 12°. (Library Handbooks, no. 6.)

B R O W N, Margaret Wright. Mending and repair of books. Chicago: American Library Association Publishing Board, 1916. 3. ed. revised by Gertrude Stiles. 23 p. 12°. (Library Handbooks, no. 6.)

B R O W N E, Frank. The preservation of books in hot climates. (Scientific American Supplement. v. 56, p. 23095. New York, 1903.)

B R O W N E, Frank. Preservation of books in hot climates: suggestions for the tropics. (Scientific American Supplement. v. 65, p. 79. New York, 1908.)

B U C K, Mitchell Starrett. Book repair and restoration; a manual of practical suggestions for bibliophiles, including some translated selections from

## The Care and Repair of Books

Essai sur l'art de restaurer les estampes et les livres, par A. Bonnardot, Paris, 1858. Philadelphia: N. L. Brown, 1918. 126 p. incl. front., illus. pl. facsim. 12°.

CHIVERS, Cedric. How to open a new book. (Library. London, 1900. ser. 2, v. 1, p. 323-326.)

CHIVERS, Cedric. The relative value of leathers and other binding materials. Brooklyn, 1911. 16 l. incl. diagrams, tables. illus. 8°.

Summary of a lecture delivered before the American Library Association at Pasadena, California, May 23, 1911, supplemented by further facts and illustrations included in a lecture given to the British Library Association at Perth, September 5, 1911.

Reprinted from the American Library Association Bulletin, July, 1911, and the Library Association Record, December, 1911.

COCKERELL, Douglas. Leather for bookbinding. (Journal of the Society of Arts. London, 1900. v. 48, p. 401-407.)

COCKERELL, Douglas. Bookbinding, and the care of books: a textbook for bookbinders and librarians. London: J. Hogg, 1901. 2 p. l., vii-xvi, 17-342 p. 12°. (Artistic crafts series of technical handbooks, no. 1.)

COCKERELL, Douglas. Bookbinding, and the care of books: a textbook for bookbinders and

## Some Other Books

librarians. With drawings by Noel Rooke, and other illustrations. London: Sir I. Pitman & Sons, Ltd. [1920] 4. ed. xvi, 17-341 p. front., illus., plates. 12°. (Artistic crafts series.)

D A V E N P O R T, Cyril. Leather as used in book-binding. (Library. London, 1898. v. 10, p. 15-19.)

G R E A T B R I T A I N.—Department of Scientific and Industrial Research. The cleaning and restoration of museum exhibits. First [to] third report upon investigations conducted at the British Museum. London, 1921, 1923, 1926. 8°.

G R Ü N E W A L D, Max. Über die Pflege des Buches in hygienischer Beziehung. (Schweizerisches Gutenbergmuseum. Bern, 1929. Jhrg. 15, p. 91-92.)

H A L L E R, Max. Die Schmiermittel-Industrie, nebst einem Anhang: Leder-Appretur und Konservierung. Leipzig: B. F. Voigt, 1925. xii, 141 p. incl. tables. 8°. (Die Werkstatt. Bd. [11A])

H A R R I S O N, T. The care of books. (The book-collector's quarterly. no. 3, p. 1-14. London, 1931.)

H A S L A M, W. The book of trade secrets, recipes and instructions for renovating, repairing, improving and preserving old books and prints. By an expert. London: J. Haslam & Co., Ltd., New York, R. R. Bowker Co., 1910. [2. ed.] 43 p. 12°.

## The Care and Repair of Books

H A S L A M, W. The library handbook of genuine trade secrets and instructions for cleaning, repairing and restoring old manuscripts, engravings and books, as practised by the experts. London: W. & G. Foyle, Ltd. [1923] 51 p. 12°.

H U C K, Thomas W. Book pests and book and print restoration. (Library Association Record. London, 1913. v. 15, p. 165-177.)

H U L M E, E. Wyndham, and others. Leather for libraries. By E. W. Hulme, J. G. Parker, A. Seymour-Jones, C. Davenport, and F. J. Williamson. London: The Sound Leather Committee of the Library Association, 1905. 57 p., 1 l. 8°.

Samples of leather on inside of covers.

H U T C H I N S, C. I. The true art of restoration of books and bindings. (Bibliophile, London, 1908. v. 1, p. 301-306.)

I N T E R N A T I O N A L Institute of Intellectual Cooperation. Conservation des manuscrits et imprimés. (Point 5 de l'ordre du jour.) [n. p., 1928.] 9, 3, 4 f., F°.

Mimeographed "Resolutions," "Vœu," and "Rapport" of the Committee of Experts for the Preservation of Printed Matter and Manuscripts.

K I D D, Donald M. Bookcraft, a new industrial art

## Some Other Books

subject; the time tested Toronto method of library book repairing adapted to school use. Syracuse, N. Y.: Gaylord Brothers, Inc., 1926. 32 p. illus. 8°.

K I D D, Donald M. The Toronto method of book repairing. Syracuse: Gaylord Brothers, 1927. 3. ed. rev. and enl. 20 p. illus. 8°.

K I M B A L L, Arthur R[ichmond]. The care of books, with special reference to fine bindings. 6 p., 1 l. 4°.

Reprinted from Medical Library Association Bulletin, January, 1912.

L A D E W I G, Paul. Bücherbeschädigung und ihre Abwehr. (Blätter für Volksbibliotheken und Lesehallen. Leipzig, 1914. Jhrg. 15, p. 109-120.)

L A M B, M. C. Leather Dressing, including Dyeing, Staining and Finishing. London: Anglo-American Technical Co., Ltd., 1925. 3. ed. xii, 472 p. 8°.

L E A T H E R for Bookbinding. (Library Association Record. London, 1900. v. 2, p. 250-253.)

L I B R A R Y A S S O C I A T I O N [British]. The durability of paper. Report of the special committee set up by the Library Association. London: The Library Association [1930]. 24 p. 8°.

## The Care and Repair of Books

Work of a committee of twelve, Arundell Esdaile, Secretary of the British Museum, chairman. The cover is printed on a Grade 1 (a) stock as specified in the report, the title page and the postscript on a Grade 1(b), the text on a Grade 2 stock.

L O N C H A M P, F.-C. *Therapeutica graphica*, ou l'art de collectionner, de conserver et de restaurer les dessins, les manuscrits, les estampes et les livres. Orné de 6 planches hors texte, enrichi d'un supplément de Recettes éprouvées et complété par un index détaillé des matières. Paris et Lausanne: Librairie des Bibliophiles, 1930. 120 p., 2 l. 12°.

L O U B I E R, Jean. Über praktische Vorkehrungen zum Schutze von Einbänden und Einzelblättern. (Centralblatt für Bibliothekswesen. Leipzig, 1901. v. 18, p. 380-387.)

L O U B I E R, Jean. Bericht der Lederkommission; Bericht über Einbandleder. (Zentralblatt für Bibliothekswesen. Leipzig, 1911. Jhrg. 28, p. 390-396.)

M U S S - A R N O L T, William. *Maneant sua data libellis: a protest and plea*. (Bibliographical Society Papers. Chicago, 1919. v. 13, p. 128-147.)

P A R K E R, J. Gordon. *Leather for bookbinding*. (Soc. of Arts. Jour. London, 1902. v. 50, p. 25-35.)



## Some Other Books

P A R L E Y, Norman. Enduring paper. (The book-collector's quarterly. no. 3, p. 29-38. London, 1931.)

P I C C I N I, Augusto. La conferenza internazionale per la conservazione degli antichi codici. (Archivio storico italiano. Firenze, 1899. ser. 5, v. 23, p. 324-329.)

P [ L E N D E R L E I T H ], H. J. Laboratory notes: The preservation of bookbindings. (British Museum Quarterly. London, 1927. v. 3, p. 77-78.)

P L E N D E R L E I T H, H. J. The preservation of leather. (Museums Journal. London, 1928. v. 27, p. 217-218.)

P O L Z E R, William. Das Zusammensetzen zerrissenen Papiere. (Archiv für Kriminal-Anthropol. und Kriminalistik. Leipzig, 1911. Bd. 43, p. 128-138.)

P O W E L L, G. H. The care of books. (Fortnightly Review. London, 1902. v. 77 (n. s. v. 71), p. 415-426.)

P R I N T I N G     I N D U S T R Y     R E -  
S E A R C H   A S S O C I A T I O N. Durability of Paper. London, 1931. 7 p. (Memorandum No. 1.)

R E S T O R A T I O N of Old Books. (Philobiblion. New York, 1862. Sept., 1862. p. 227-229.)

## The Care and Repair of Books

Recipes for removal of grease, ink, washing or other purposes, general remarks on restoration.

R I E S E N F E L D, E. H., and T. H. Hamburger. Ueber die Zerstörung von Papier durch Licht und deren Verhinderung. (Zentralblatt für Bibliothekswesen. Nov., 1930. Jhrg. 47, p. 604-609.)

R I S - P A Q U O T, [Oscar Edmond]. Guide pratique du restaurateur-amateur de tableaux, gravures, dessins, pastels, miniatures, etc., reliures et livres, suivi de la manière de les entretenir en parfait état de conservation. Paris: H. Laurens, 1890. 2 p. l., 260 p., 8 fac., 2 pl. illus. 8°.

R O T H, Ernst. Ueber den Zerfall der ledernen Bucheinbände. (Centralblatt für Bibliothekswesen. Leipzig, 1902. v. 19, p. 469-471.)

R O Y A L S O C I E T Y O F A R T S. Report of committee on leather for bookbinding. (Society of Arts. Journal. London, 1901. v. 49, p. 621-638.)

R O Y A L S O C I E T Y O F A R T S, London, and the Worshipful Company of Leathersellers. Report of the committee on leather for bookbinding. London: Society of Arts, 1905. 5 p. l., 120 p., 1 l., 2 pl. 4°.

R Y E, W. B. Leather for bookbinding. (Library Association Record. London, 1901. v. 3, p. 532-534.)

## Some Other Books

S É E, Pierre. Les maladies du papier piqué; les champignons chromogènes, qui les provoquent, les modes de préservation. Paris: O. Doin et fils, 1919. 1 p. l., 168 p., incl. tables. 17 pl. (1 col., 1 fold.) 8°. ST AND AGE, H. C. Leather for bookbinding. (Society of Arts. Journal. London, 1900. v. 48, p. 458-459.)

STRAIGHT, Maude W. Repairing of books. (Public Libraries. Chicago, 1900. v. 5, p. 88-89.)

SUSSEX ARCHÆOLOGICAL SOCIETY. Report of a committee on permanency of printing papers. (Sussex Archæological Collections. Cambridge, 1930. v. 71, p. xlix-lix.)

Dated 6th July, 1929.

VEITCH, Fletcher Pearre. The care of leather. Washington: Government Printing Office, 1920. 18 p. 8°. (United States Department of Agriculture. Farmer's Bulletin 1183.)

VEITCH, Fletcher Pearre. Paper-making materials and their conservation. Washington: Government Printing Office, 1911. 20 p. 8°. (United States. Chemistry Bureau. Circular 41.)

First issued Dec. 31, 1908. Reprinted Mar. 31, 1909, Jan. 31, 1911.

VEITCH, Fletcher Pearre. Suitable paper for

## The Care and Repair of Books

permanent records. (Yearbook of the United States Department of Agriculture. 1908. Washington, 1909. p. 261-266.)

VEITCH, F. P., and others. Polluted atmosphere a factor in the deterioration of bookbinding leather. (American Leather Chemists Association. Journal. Easton, Pa., 1926. v. 21, p. 156-176. illus., pl., tables.)

Also reprinted separately.

VEITCH, F. P., and R. W. Frey. Preservation of leather bookbindings. Washington: Government Printing Office, 1930. 8 p. 8°. (United States Department of Agriculture. Leaflet, no. 69.)

VREESE, Willem de. Het Zapon. Een nieuw middel om handschriften en boeken te herstellen en tegen vernietiging te vrijwaren. (Tijdschrift voor Boek- en Bibliotheekwezen. Antwerpen, 1903. Jaarg. 1, p. 69-82.)

WALTON, Robert P. Causes and prevention of deterioration in book materials. (New York Public Library. Bulletin. New York, 1929. v. 33, p. 235-266.)

WALTON, Robert P. Causes and prevention of deterioration in book materials. New York: The New York Public Library, 1929. 39 p. 8°.

WALTON, Robert P. Preserving newspaper files. (Scientific American. January, 1931. p. 31.)

## Some Other Books

W A R N E R, John. Modern bookbinding leathers. (Library Association Record. London, 1929. n. s., v. 7, p. 153-164.)

Bibliography, p. 163. Notes by W. D. John, p. 163-164.

W H E A T L E Y, Henry Benjamin. Leather for bookbinding. (Library. London, 1901. ser. 2, v. 2, p. 311-320.)

W I L E Y, H[arvey] W[ashington], and C. H. Merriam. Durability and economy in papers for permanent records. A report submitted by H. W. Wiley and C. Hart Merriam, including paper specifications, by F. P. Veitch. Washington: Government Printing Office, 1909. 51 p. illus. 8°. (United States. Agriculture Department. Report 89.)

W I R E, George E. Leather preservation [an enthusiastic argument in favor of treatment by vase-line]. (Library Journal. New York, 1928. v. 53, p. 586-589.)

Y V E - P L E S S I S, R. Petit essai de bibliothérapeutique; ou, L'art de soigner et restaurer les livres vieux ou malades. Paris: H. Daragon, 1900. 2 p. l., 95 p., 1 l. 12°. (Collection du bibliophile parisien.)

250 copies printed.





# INDEX

- A** Accession records, 15  
 Acids in tanning leather, 91  
 Air, Disease germs in, 25-26  
 Air, Effect of, on books in exhibition cases, 19  
 Air, Harmful effects on books, 21-25  
 Air, Polluted, 24-25, 91  
 Air conditioning, 23, 92  
 Alcohol for cleaning vellum, 82  
 Alcohol for removal of mold or mildew, 28  
 Alcohol for removal of stains, 69  
 Alcohol for removal of varnish, 61  
 Ammonia as paper bleach, 75  
 Anatomy of the book, 33  
 Aniline dye for coloring paper, 74  
 Animal oil, Effect on leather, 100  
 Anthrax, Books subjected to, 26  
 Artificial leather, Color in, 105
- B** Backs of books, 49-56  
 Bands, Books sewed on, 33, 49  
 Bedbugs in books, 20  
 Beeswax, 97, 99  
 Benzene for cleaning, 61, 68, 82, 106  
 Benzole for cleaning, 68, 106  
 Bicarbonate of soda as paper bleach, 75  
 Bleaching of paper, 73-74  
 Bleaching of vellum, 81  
 Book cloth, Restoration, 57  
 Book disinfection, 25-26  
 Book supports, 17  
 Bookplates, 15  
 Bookworms, 27  
 Borers, Attack on books, 27  
 British Museum leather dressing, 97-99  
 Brushes, Paste and Glue, 39-40, 41  
 Cambric for book repair, 41
- C** Canton flannel for recasing of books, 50  
 Care of books, 9-20  
 Castile soap, 94  
 Castor oil for leather dressing, 94  
 Catalogue records, 15  
 Cedarwood oil, 97  
 Cellophane as covering material, 46  
 Chiffon for covering paper, 43-45  
 Chlorinated potash as paper bleach, 75  
 Chrome tanned leather, 91, 102  
 Cleaning of books, 29  
 Cleaning of paper, 68-79  
 Cloth, Book, Restoration, 57  
 Cloth bindings, Treatment of, 104-107  
 Cloth for book repair, 41  
 Cloth for dusting books, 28-29

# Index

- Coated paper, 69  
 Cockroaches in books, 26  
 Coffee solution for coloring paper, 74  
 Collating, 14  
 Colored bindings, 104-107  
 Colored inks, Treatment of, 78  
 Colored prints, Treatment of, 77-78  
 Coloring of paper, 74  
 Conditioning of air, 23  
 Cords, Books sewed on, 33, 49  
 Corners, Repair of, 48  
 Corrosive sublimate as disinfectant, 27  
 Covering with silk or tissue paper, 43-46  
 Covers, Loose, 48
- D** Dampness, Harm to books, 22  
 Darkness affecting books, 11  
 Dealers in bindery materials, 63-64  
 Dealers in chiffon and tissue paper, 45  
 Diphtheria, Books subjected to, 26  
 Disease germs, Effect on books, 25-26  
 Disinfection of books, 25-26  
 Dough as an eraser, 68  
 Dressings for leather, 92-103  
 Dry air, Effect on books, 22-23  
 Dust cloths for books, 29  
 Dusting of books, 29
- E** Egg oil dressing, 99  
 Eggio, 99  
 Encephalitis lethargica, Books subjected to, 26  
 Enemies of books, 21-31  
 Equipment for repair of books, 40-41  
 Erasers, 68, 82, 106  
 Ethics of repair work, 53, 66  
 Exhibition cases, Care of books in, 19  
 Fever, Typhoid, Books subjected to, 26  
 Filling of holes, 48, 67  
 Fire damage, 59-60  
 Fire danger from fumes, 69  
 Flannel for recasing of books, 50  
 Folders, Bone, 40  
 Fore edge damage, 19  
 Formaldehyde as disinfectant, 27  
 Foxing of paper, 72-73  
 Frey, R. W., 95  
 Furniture polish for leather dressing, 99  
 Gas fumes, Effect on leather, 101-102  
 Gasolene for removal of grease stains, 68  
 Gelatine for resizing paper, 70-72  
 Glass as protection for books on exhibition, 19  
 Glass sheet for repair of books, 41  
 Glue, 34-40  
 Grease stains, Removal of, 68, 106  
 Gum as an eraser, 68, 106  
 Gummed tissue paper, 42  
 Handling books, 19-20  
 Harm to books, 21-31
- F**
- G** Heat, Dry, to drive away mildew or mold, 28  
 Heated air, Effect on books, 22-23  
 Hexane, 97  
 Hinges of books, 49  
 Holes in paper, Filling of, 48, 67
- H**

# Index

- Hollow backs, 51-52  
Housecleaning damage to books, 19, 29  
Housing conditions for books, 11  
Humidity control, 22-24  
Humidity favorable to mildew or mold, 28  
Hydrochloric acid for bleaching paper, 74  
Hydrogen peroxide as paper bleach, 75  
Hygrometer for testing humidity, 24
- I** Infection traced to books, 25-26  
Ink, White, 61  
Ink removal, 60-61  
Inks, Effect on, when paper is bleached, 79  
Insecticides for books, 27  
Interleaving, 56  
Iodine stains removed by alcohol, 69  
Isinglass for resizing paper, 70-72
- J** Japan Paper Company, 45  
Japan wax, 95  
Javelle water as paper bleach, 75  
Joints of books, 49
- K** Kerosene for removal of stains, 68  
Knives, 40
- L** Labels, 57  
Lacquers on bindings, 105-106  
Lanolin for leather dressing, 93-97  
Lanolin for softening vellum, 83  
Large books, Shelving of, 19  
Leather, Artificial, 105  
Leather affected by polluted air, 91  
Leather backs of books, 53-56  
Leather dressings, 92-103  
Leather polishing, 93-98, 99  
Leather treatment, 90-103  
Leaves, Loose, 47  
Lettering, Restoration of, 79  
Loose backs, 51-52  
Loose covers, 48  
Loose leaves, 47  
Mending of books, 31-64  
Meningitis, Books subjected to, 26  
Mice, Attack on books, 27  
Mildew on books, 22, 28, 69  
Mineral oil, Effect on leather, 100  
Mold on books, 22, 28  
Mold stains removed by alcohol, 69  
Moving of books, 19-20  
Muslin for recasing of books, 50  
Neat's foot oil leather dressing, 93-97  
Neat's foot oil for vellum softening, 83  
Neutralizers in bleaching paper, 76  
Newspaper repair, 42-43  
New York City Health Department disinfection of books, 26  
Newspapers, Repair of, 42-45
- O** Oberfelder, Albert E., 45  
Oil, Castor. See Castor oil  
Oil, Cedarwood. See Cedarwood oil  
Oil, Egg. See Egg oil  
Oil, Neat's foot. See Neat's foot oil  
Oil stains, Removal of, 68  
Oil treated cloths for dusting books, 29  
Opening a book, 13-14
- M**
- N**

# Index

- Ownership marks, 15-16  
 Oxalic acid as paper bleach, 75  
**P** Pages, Torn, Repair of, 41-42  
 Palm leaf manuscripts, 88-89  
 Paper, Coated, 69  
 Paper bleaching, 73-74  
 Paper cleaning, 68-79  
 Paper coloring, 74  
 Paper for mending, 65-66  
 Paper sizing, 70-72  
 Paper treatment, 65-79  
 Paper used in book repair, 41  
 Paper washing, 69  
 Papyrus, 84-88  
 Parchment, Treatment of, 80-83  
 Paste, 35-40  
 Paste making, 37-38  
 Paste, Care in pressing after its use, 39  
 Perforating stamps, 16  
 Pitch stains, 61  
 Plaster of Paris in bleaching paper, 75  
 Pliny on papyrus, 85  
 Poliomyelitis, Books subjected to, 26  
 Polluted air, 24-25  
 Potash, Chlorinated, as paper bleach, 75  
 Potassium for bleaching paper, 73-74  
 Press for book repair, 41  
 Pressing, Need for, after use of paste and glue, 39  
 Preventive control of books, 30  
 Prints, Treatment of, 77-78  
 Protection by means of silk or tissue covering, 43-45  
**R** Rats, Attack on books, 27  
 Rebacking, 52-56  
 Recasing a book, 50  
 Repair of books, 32-64  
 Repair equipment, 40-41  
 Repairing books, Ethics of, 53, 66  
 Resizing of paper, 70-72  
 Restoring lettering, 79  
 Roller shelves, 19  
 Rubber erasers, 68, 81, 106  
 Rubber stamps, 16  
 Rubricated letters, Restoration of, 79  
 Saddle dressing, 99  
 Scarlet fever, Books subjected to, 26  
**S** Scissors, 40  
 Sealing wax, 62  
 Septic sore throat, Books subjected to, 26  
 Shellac removed by alcohol, 61  
 Shelving of books, 16-17  
 Silk chiffon for covering paper, 43-45  
 Sizing of paper, 70-72  
 Slip covers, 62  
 Smallpox, Books subjected to, 26  
 Soap, Castile, 94  
 Soap for cleaning vellum, 81  
 Soap for washing paper, 69  
 Soda bicarbonate as paper bleach, 75  
 Soda sulphite as paper bleach, 75  
 Sodium stearate, 95  
 Solander covers, 62  
 Sperm oil, 95  
 Sponges, 41  
 Sponges used for air conditioning, 23  
 Spring backs, 51-52  
 Stains, Removal of, 68  
 Stamps for ownership marking, 16

# Index

- Steam for softening vellum, 83  
 Straight edge, 41  
 Sulphite of soda as paper bleach, 75  
 Sunshine, Effect on books, 11  
 Super for book binding, 33, 49  
 Supervision of books, 30  
 Supply houses for bindery materials, 63-64  
 Supply houses for chiffon and tissue paper, 45  
**T** Tallow for leather dressing, 94  
 Tar stains, 61  
 Tea solution for coloring paper, 74  
 Throat, Septic sore, Books subjected to, 26  
 Thymol, 28  
 Tight backs, 52  
 Tissue paper, Gummed, 42  
 Tissue paper for covering, 43-45  
 Torn pages, Repair of, 41-42  
 Transparent materials, 46  
 Treatment of paper stock, 65-79  
 Tuberculosis, Books subjected to, 26  
 Turpentine for leather dressing, 95  
 Turpentine for removal of pitch stains, 61  
 Typhoid fever, Books subjected to, 26  
 Vacuum cleaners, 29  
 Varnish removed by alcohol, 61  
 Varnishes on bindings, 105-106  
 Vaseline, 100  
 Vegetable oil, Effect on leather, 100  
 Veitch, Fletcher Pearre, 95  
 Vellum, Treatment of, 80-83  
 Vellum bleaching, 81  
 Warped vellum covers, 83  
 Washing of paper, 69  
 Water colors, Treatment of, 78  
 Water in leather dressing, 95  
 Water soaked books, 58  
 Wax removal, 61  
 Waxed paper as preventive of leaves sticking together, 47  
 Weakening of paper by bleaching, 76  
 Weights for book repair, 41  
 White ink removal, 61  
 Wrinkled vellum, 82  
**Z** Zinc, Sheet, 40












Z700 .L98

The care and repair of books

Princeton Theological Seminary-Speer Library



1 1012 00147 3240